

CHAPTER VI
ORIENTED NaA ZEOLITE MEMBRANE FORMATION AND
PERFORMANCE USING SEEDING AND ELECTROPHORETIC
TECHNIQUES

(Submitted to *International Journal of Applied Ceramic Technology*)

6.1 Abstract

Oriented NaA zeolite membranes have been successfully fabricated on a tubular α -Al₂O₃ support by secondary growth under electrical field. A uniform and dense columnar LTA crystal layer was formed. The XRD pattern shows the strong {222} peak of the preferred orientation. The effects of seeding time and electrical potential on the performance of the membrane were investigated. It was found that a high quality NaA zeolite membrane prepared using 1.5 min seeding time before crystallization at 333 K under 2V electric field gave the best membrane performance with a separation factor greater than 10,000 and 0.61 kg/m².h in flux.

Keywords: Zeolite membrane, Orientation, Columnar crystal, Morphology and Pervaporation

6.2 Introduction

Recently, zeolite membranes have attracted a great deal of attention due to their uniform microporous structure, good thermal stability, high mechanical strength, and high resistance to relatively extreme chemical environments^{1,2}. Several methods have been used to synthesize the membranes, such as hydrothermal synthesis³⁻⁶, secondary growth⁷⁻⁹, microwave synthesis¹⁰⁻¹², and the electrophoretic technique^{13,14}. The hydrothermal method usually needs only a single step; however, it was found to have some disadvantages, such as difficulty in controlling the nucleation on the surface support¹⁵. The obtained membranes are randomly oriented. Another technique in making a NaA zeolite membrane, called the secondary growth or seeding method, has been introduced as an alternative approach to grow zeolite crystals preferentially on a support surface¹⁶. Different techniques were used to attach the seed crystals onto the substrate, viz. rubbing¹⁷, treating the supporting with a cationic polymer before deposition of the crystal seeds¹⁸⁻¹⁹, dip coating²⁰⁻²⁴, and vacuum seeding^{25,26}.

Microwave synthesis is an alternative not only for limiting the synthesis duration, but also for improving the properties of the zeolite membrane²⁷⁻²⁹. However, the performance of the zeolite membrane prepared by this method still fluctuates without the aid of the seeding technique³⁰.

Electrophoresis deposition has been found to be a simple and effective technique for thin film preparation^{31,32} although it takes longer period of reaction time than the microwave technique. The charged particles can migrate to the support surface homogeneously and rapidly under the action of the applied electric field, resulting in uniform and dense membranes³⁰. This technique is not only for coating the charged particle on the substrate before hydrothermal treatment, but is also for driving the zeolite particles to migrate to the support surface during hydrothermal synthesis^{19,33,34,35}, resulting in the formation of an oriented, continuous layer of zeolite seeds on the support to act as nuclei for the crystal growth step¹⁵.

In this paper, we demonstrate that, with the aid of the seeding technique, highly oriented NaA zeolite membranes can be prepared on α -Al₂O₃ support using the electrophoretic technique. The effects of potential and crystal seeds on membrane

morphology and thickness were investigated, and the performance of the synthesized membranes, relative to those effects, is also studied using the pervaporation technique.

6.3 Experimental

6.3.1 Materials

Fumed silicon dioxide (SiO_2 , surface area $474 \text{ m}^2/\text{g}$, average particle size $0.007 \text{ }\mu\text{m}$) and aluminum hydroxide hydrate ($\text{Al}(\text{OH})_3 \cdot x\text{H}_2\text{O}$, surface area $51 \text{ m}^2/\text{g}$) were purchased from Aldrich, Co. Sodium hydroxide (NaOH) from Lab-Scan Co., Ltd. was used as the base catalyst. Homemade porous α -alumina tubes (11 mm outer diameter, 9 mm inner diameter, 6 mm length, $0.3 \text{ }\mu\text{m}$ pore radius on average with 38 % porosity) were used as supports and were supplied by MTEC.

6.3.2 Equipment

All samples were characterized using scanning electron micrographs (SEM) on a JEOL 5200-2AE (MP15152001) and wide angle X-ray diffractograms (WXR) on the D/MAX 2000 series of the Rigaku X-Ray Diffractometer system using $\text{CuK}\alpha$ as a source. The membrane synthesis was performed using microwave on a Milestone, Ethos SEL Spec 1000 W and 2450 MHz. The separation factor calculated from the quantities of water and ethanol was determined using gas chromatography (Win Lab III, Perichorm).

6.3.3 NaA zeolite membrane synthesis

The porous Al_2O_3 tube was cleaned and washed with deionized water by ultrasonication for 15 min to remove any dirt on the surface. The cleaned support was dried at 363 K for 24 h and calcined at 673 K for 3 h to burn off any impurities on the support surface before coating with seed crystals. Membrane synthesis was carried out by first coating the NaA zeolite crystal on the alumina substrate, followed by immersing the coated substrate into a vessel containing the solution mixture for further microwave heat treatment.

Vacuum seeding²⁵ was used to coat the NaA seed onto the support tube. The suspension was prepared by dispersing 7 g of NaA zeolite (particle size ~0.1-0.2 μm) synthesized using the $\text{SiO}_2\text{:Al}_2\text{O}_3\text{:3Na}_2\text{O:410H}_2\text{O}$ formula described in ref. 35, into 1000 ml of water with ultrasonic treatment. The seeding layer was coated onto the outer surface of the support tube using 0.0325 MPa for 1.5, 2, and 3 min. The seeded support was dried in air at 383 K for 24 h before characterization using SEM.

The clean Al_2O_3 tubes were placed vertically in a stainless steel autoclave containing the precursor solution ($5\text{SiO}_2\text{:Al}_2\text{O}_3\text{:50Na}_2\text{O:1000H}_2\text{O}$), prepared according to ref. 36, and using an electric field, as studied in ref. 15. After crystallizing at 333 K for 10 h, repeated synthesis (multistage synthesis) was carried out in order to improve the quality of the NaA zeolite membrane. The synthesized membrane was washed several times with deionized water and then dried in air at 363 K for a few day before characterization using SEM and XRD.

6.3.4 Pervaporation

The efficiency of the synthesized membrane on the support tube was determined, including the separation factor and the water flux, by the pervaporation, using an ethanol/water mixture (95/5) at a feed rate of 0.898 l/min, 10 mmHg vacuum pressure, and 343 K. The quantities of the water and the ethanol were determined by a gas chromatograph equipped with an HP plot Q capillary column at 433 K TCD detector temperature and 180 kPa helium gas flow rate.

6.4 Results and Discussion

6.4.1 NaA Zeolite Formation on the Support

The most important factor during zeolite membrane formation under electric field is the surface attractive force of the zeolite particle on the support¹⁵. Before crystallizing, the $\alpha\text{-Al}_2\text{O}_3$ support was seeded using 7 g/l of the NaA zeolite (0.1-0.2 μm) in water for 2 min seeding time. Figure 6.1 is the SEM images of the synthesized NaA zeolite membranes prepared by hydrothermal synthesis (Fig. 6.1

b,c) and electrophoretic technique (Fig. 6.1 d,e) using electric potential (1.0 V) and heating at 333 K for 10 h. As can be seen from the SEM results, more uniform crystals were formed on the support surface when using the electrophoretic technique while less uniform crystals with a size of about 1-3 μm and a thickness of about 12-13 μm were obtained when using microwave heating. The reason for this less-uniform crystal formation in hydrothermal heating is that zeolite particles are generated and irregularly and slowly transported to the support surface by the action of gravity and the hydrodynamic effect¹⁵.

For the electrophoretic technique, the seeded support surface provided enough nuclei for crystals to grow during hydrothermal treatment. When applying an electric field, the charged zeolite particles migrate onto the support surface orderly and regularly, providing a uniform and dense zeolite membrane, as shown in Fig. 6.1 d,e. After crystallization, the crystal sizes (about 1-2 μm) became uniform on the support surface and covered it thoroughly with 13-14 μm thickness.

The XRD patterns (Fig. 6.2) show that NaA zeolite synthesized using the electrophoretic technique was fabricated and it produced (see the reflection of {222}) oriented-like membrane³⁷. Furthermore, the columnar LTA crystal layer was clearly observed in the SEM result (Fig. 6.1 e). The oriented membrane was obtained by gradually and orderly moving negatively-charged NaA zeolite to the support within the applied field³⁸.

6.4.2 Effect of Seeding Time on Membrane Properties

The seeding, or secondary growth, method involves the deposition of zeolite nanosized seed crystals on the substrate before hydrothermal growth, leading to the formation of an inter-grown film. It is well known that the presence of seeds on the support surface provides better control of the membrane formation process by forming a gel layer over the seed layer, causing crystal nucleation and growth with shortened crystallization time^{25, 39, 40}.

In addition, the secondary growth method ensures the growth of the zeolite crystals on the support rather than in the solution and limits the nucleation from transforming to other crystals^{41,42}. However, the most important factor in zeolite

membrane preparation is the fabrication of a very thin film with a defect-free membrane layer in order to obtain a high efficiency of flux and separation. The seeds indeed have a significant effect not only on the quality, but also on the performance of the synthesized membrane. In our study, we fix the seed concentration and vary the seeding time (1.5, 2, and 3 min). Figure 6.3 b-d is the SEM images of Al_2O_3 substrates coated with 7 g/l of the seed in water at a coating pressure of 0.0325 MPa for 1.5, 2, and 3 min coating time, respectively. It can be clearly seen that 1.5 min seeding time was enough to completely cover (Fig. 6.3 b) the substrate. The longer time, especially the 3 min seeding time, resulted in a denser layer.

Figure 6.4 presents the SEM images of the synthesized NaA zeolite membrane fabricated by the electrophoretic technique using 2 V electric potential at 333 K for 10 h. It was found that the seeding time influences the membrane thickness. All of the coating times gave a fully covered $\alpha\text{-Al}_2\text{O}_3$ support surface with homogeneous NaA zeolite crystals (1-2 μm). The membrane thickness was about 15-17 μm . The longer the seeding time (3 min) was the denser and the thicker the membrane obtained was. A possible explanation is that the secondary growth of the NaA seeds seals the inter-crystalline gaps and forms a continuous and tightly-packed film. In fact, this phenomenon is necessary for membrane application⁴³.

Figure 6.5 shows the diffraction patterns of the synthesized membrane fabricated for different seeding times (1.5, 2, and 3 min) on the $\alpha\text{-Al}_2\text{O}_3$ support before crystallizing under applied electric field. The diffraction patterns of all membranes contain the peaks of $\alpha\text{-Al}_2\text{O}_3$ support and NaA zeolite, indicating that only pure NaA zeolite membranes were obtained. All NaA zeolite membranes show the strong {222} peak in the XRD pattern, indicating the preferred orientation in the overall membrane, ranging from the surface to the porous alumina support layer³⁷.

6.4.3 Effect of Applied Electric Potential on Membrane Properties

Shan *et al.*³² fabricated the zeolite film by electrophoretic deposition in a non-aqueous medium and investigated the effect of voltage and time on the zeolite film. They reported that the film thickness increased with higher voltage at the same deposition time, similar to the work done by Huang *et al.*¹⁵. For our case,

the SEM images of the synthesized NaA zeolite membrane prepared by the electrophoretic technique at 333 K for 10 h with different electrical potentials (1-2 V) also show the same trend. It can thus be concluded that the applied electrical potential has a great effect on the thickness of the synthesized NaA zeolite membrane. The SEM image (Fig. 6.6 a) shows that, at 1.0 V the α -Al₂O₃ substrate was fully covered with the NaA zeolite with 1-3 μ m crystals and 13-14 μ m thickness. With increasing the electrical potential, the synthesized membranes became denser, with columnar characteristics, and thicker (Fig. 6.6 c-f). This is owing to the particles possessing higher electric mobility in the more intensive electric field³². At 2.0 V electric field (Fig. 6.6 e,f) the membrane became more packed and the crystal seemed to be smaller because the zeolite particles migrate on the surface rapidly before growing into larger ones¹⁵. The thickness of the zeolite membrane was also increased to 17-18 μ m.

6.4.4 Effect of Applied Electric Potential on Membrane Performance

According to well-defined properties for separation purposes, the coating layer should be as thin as possible and free of any pinholes for optimal performance³⁹. Thus, controlling the thickness and the texture of the membrane is a significant task in determining the performance of the system. Characterization using XRD and SEM can only indicate whether a continuous membrane forms on the support, but cannot confirm whether a defect-free zeolite membrane was obtained. To evaluate the quality of the synthesized membranes, the pervaporation technique was used. Table 6.1 summarizes the effects of the seeding time and the electrical potential on the membrane performance. Without application of the electrical field, the formation of the NaA zeolite membrane is promoted by the seed layer on the support surface. The zeolite nuclei forms gel layers and grows into zeolite crystal, followed by inter-growth of the zeolite crystals to eventually form a membrane^{35, 37}. As shown in Table 6.1, the seeding time has a great effect on the zeolite membrane performance. When the seeding time is too long, the seeding layer is too thick, creating cracks which result in poor separation properties. On the contrary, when the seeding time is short, the seed amount on the support is not enough to produce a sufficient number of nuclei to convert into a denser zeolite film, also resulting in

poor performance. The suitable seeding time for the hydrothermal treatment is 2 min, giving a much better performance with a separation factor $>10,000$. Under the action of the electric field and hydrothermal treatment, a more uniform and denser zeolite membrane was formed, especially, at the highest electric field; and the best performance was obtained. This is because the charged particles can migrate to the support surface homogeneously and rapidly¹⁵. As discussed previously, the applied electrical potential plays a significant role in the crystal growth and the membrane thickness^{15,32}. The pervaporation results in Table 6.1 indicate that under the same electric field potential, the 1.5 min seeding time provided the best quality membrane, while a longer seeding time caused the membrane to be too thick, creating cracks and providing poor performance.

6.5 Conclusions

Oriented, uniform, and dense NaA zeolite membranes were successfully prepared on an alumina substrate by seeding and electrophoretic techniques. Both the morphology and the performance of the membranes were improved. The applied electric potential has an important effect on the membrane layer, as well as on the membrane thickness, of the NaA zeolite. More homogeneous and more uniform crystals were formed on the alumina support surface, with a size of 1-3 μm . With increasing applied electrical potential, smaller crystal sizes and denser NaA zeolite membranes were obtained, with better performance. The seeding time is also responsible for the zeolite membrane thickness and performance. A longer seeding time generates a NaA zeolite membrane that is too thick and contains cracks, causing poorer performance. All of the synthesized membranes were oriented-like membranes, confirmed by the strong $\{222\}$ peak in the XRD pattern. The best NaA zeolite membrane was prepared using 1.5 min of seeding time on the alumina support before crystallizing at 333 K under an electrical field of 2 V, giving a separation factor $> 10,000$ and $0.61 \text{ kg/m}^2\cdot\text{h}$ flux.

6.6 Acknowledgments

The author gratefully acknowledges the financial support of the Reverse Brain Drain Project, National Science and Technology Development Agency, Ministry of Science and Technology (Thailand); the Postgraduate Education and Research Program in Petroleum and Petrochemical Technology, PPT Consortium (ADB) Fund; the Ratchadapisake Sompote Fund, Chulalongkorn University; and, Prof. Weishen Yang, State Key Laboratory of Catalysis, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian, China.

6.7 References


1. T. Bein, "Synthesis and applications of molecular sieve layers and membranes," *Chem. Mater.*, 8 1636-1653 (1996).
2. J. Caro, M. Noack, P. Kolsch, and R. Schafer, "Zeolite membranes – state of their development and perspective," *Micropor. Mesopor. Mater.*, 38 [1] 3-24. (2000).
3. B. Oonkhanond and M.E. Mullins, "The preparation and analysis of zeolite ZSM-5 membranes on porous alumina supports," *J. Membr. Sci.*, 194 [1] 3-13. (2001).
4. X. Zhang, W. Zhu, H. Liu, and T. Wang, "Novel tubular composite carbon-zeolite membranes," *Mater.Lett.*, 58 [17-18] 2223-2226 (2004).
5. J. Zah, H. M. Krieg, and J.C. Breytenbach, Layer development and growth history of polycrystalline zeolite A membranes synthesized from a clear solution," *Micropor. Mesopor. Mater.*, 93 [1-3] 141-150 (2006).
6. J. Motuzas, A. Julbe, R.D. Noble, A.van.de. Lee, and Z. J. Beresnevicus, "Rapid synthesis of oriented silicalite-1 membranes by microwave-assisted hydrothermal treatment," *Micropor. Mesopor. Mater.*, 92 [1-3] 259-269 (2006).
7. J. Zah, H. M. Krieg, and J. C. Breytenbatch, "Pervaporation and related properties of time-dependent growth layers of zeolite NaA on structured ceramic supports," *J. Mem br. Sci.*, 284 [1-2] 276-290 (2006).
8. Y. Li, J. Liu and W. Yang, "Formation mechanism of microwave synthesized LTA zeolite membranes," *J. Membr. Sci.*, 281 [1-2] 646-657 (2006).
9. M. Pera-titus, M. Bausach, J. Llorens, and F. Cunill, "Preparation of inner-side tubular

- zeolite NaA membranes in a continuous flow system,” *Sep. Purif. Technol.*, Inpress (2007).
10. X. Xu, Y. Bao, C. Song, W. Yang, J. Liu, and L. Lin, “Synthesis, characterization and single gas permeation properties of NaA zeolite membrane,” *J. Membr. Sci.*, 249 [1-2] 51-64 (2005).
 11. X. Chen, W. Yang, J. Liu, and L. Lin, “Synthesis of zeolite NaA membranes with high permeance under microwave radiation on mesoporous-layer-modified macroporous substrates for gas separation,” *J. Membr. Sci.*, 255 [1-2] 201-211 (2005).
 12. A. Arafat, J.C. Jansen, A.R. Ebaid and H. van Bekkum, “Microwave preparation of zeolite Y and ZSM-5,” *Zeolite*, 13 [3] 162-165 (1993).
 13. T. Seike, M. Matsuda, and M. Miyake “Fabrication of Y-type zeolite films by electrophoretic deposition,” *Solid State Ionics*, 151 [1-4] 123-127 (2002).
 14. T. Mohammadi, A. Pak, Z. Nourian, and M. Taherkhani, “Experimental design in mullite microfilter preparation,” *Desalination*, 184 57-64 (2002).
 15. A. Huang, and W. Yang, “Electrophoretic technique for hydrothermal synthesis of NaA zeolite membranes on porous α -Al₂O₃ supports,” *Mater. Resear. Bull.*, 42 657-665 (2007).
 16. G. Li, E. Kikuchi, and M. Masukata, “A study on the pervaporation of water-acetic acid mixtures through ZSM-5 zeolite membranes,” *J. Membr. Sci.*, 218 [1-2] 185-194 (2003).
 17. K. Kusakabe, T. Kuroda, A. Murata, and S. Morooka, “Formation of a Y-type zeolite membrane on a porous α -alumina tube for gas separation,” *Ind. Eng. Chem. Res.*, 36 [3] 649-655 (1997).
 18. J. Hedlund, S. Mintova, and J. Sterte, “Controlling the preferred orientation in silicalite-1 films synthesized by seeding,” *Micropor. Mesopor. Mater.*, 28 [1] 185-194 (1999).
 19. L.C. Boudrea, J.A. Kuck, and M. Tsapatsis, “Deposition of oriented zeolite A films: in situ and secondary growth,” *J. Membr. Sci.*, 152 [1] 41-59. (1999)
 20. G. Bonilla, D. G. Vlachos and M. Tsapatsis, “Simulations and experiments on the growth and microstructure of zeolite MFI films and membranes made by


- secondary growth," *Micropor. Mesopor. Mater.*, 42 [2-3] 191-203 (2001).
21. G. Xomeritakis, S. Nair, and M. Tsapatsis, "Transport properties of alumina-supported MFI membranes made by secondary (seeded) growth," *Micropor. Mesopor. Mater.*, 38 [1] 61-73 (2000).
 22. S. Li, V.A. Tuan, J.L. Falconer, and R.D. Noble, "Preparation of water/THF mixtures using zeolite membranes," *Ind. Eng. Chem. Res.*, 40 4577-4585 (2001).
 23. K. Okamoto, H. Kita, K. Horii, K. Tanaka, and M. Kondo, "Zeolite NaA membrane: preparation, single-gas permeation, and pervaporation and vapor permeation of water/organic liquid mixture," *Ind. Eng. Chem. Res.*, 40 163-175 (2001).
 24. Y. Takata, T. Tsuru, T. Yoshioka and M. Asaeda, "Gas permeation properties of MFI zeolite membranes prepared by the secondary growth of colloidal silicalite and application to the methylation of toluene," *Micropor. Mesopor. Mater.* 54 [3] 257-268 (2002).
 25. A. Huang, Y.S. Lin, and W. Yang, "Synthesis and properties of A-type zeolite membranes by secondary growth method with vacuum seeding," *J. Membr. Sci.*, 245 [1-2] 41-51 (2004).
 26. S. R. Lee, Y. H. Son, A. Julbe, and J. H. Choy, "Vacuum seeding and secondary growth route to sodalite membrane," *Thin Solid Films*, 492 [1-2] 92-96 (2006)
 27. Y. Li, H. Chen, J. Liu, and W. Yang, "Microwave synthesis of LTA zeolite membranes without seeding," *J. Membr. Sci.*, 277 [1-2] 230-239 (2006).
 28. X. Xu, Y. Bao, C. Song, W. Yang, J. Liu, and L. Lin, "Microwave-assisted hydrothermal synthesis of hydroxy-sodalite zeolite membrane," *Micropor. Mesopor. Mater.*, 75 [3] 173-181 (2004).
 29. Y. Li and W. Yang, "Microwave synthesis of zeolite membranes: A review," *J. Membr. Sci.*, In Press.
 30. A. Huang, and W. Yang, "Hydrothermal synthesis of NaA zeolite membrane together with microwave heating and conventional heating," *Mater. Lett.*, 61 [29] 5129-5132 (2007).
 31. E.M. Wong, and P.C. Season, "ZnO quantum particle thin films fabricated by electrophoretic deposition," *Appl. Phys. Lett.*, 74 [20] 2939-2941 (1999).
 32. W. Shan Y. Zhang, W. Yang, C. Ke, Z. Gao, Y.F. Ye, and Y. Tang, "Electrophoretic deposition of nanosized zeolites in non-aqueous medium and its application

- in fabricating thin zeolite membranes,” *Micropor. Mesopor. Mater.*, 69 [1-2] 35-42 (2004).
33. S. Mintova, J. Hedlund, V. Valchev, B. Schoeman, and J. Sterte, “ZSM-5 films prepared from template free precursors,” *J. Mater. Chem.*, 8 2217-2221 (1998).
 34. Á. B. Murcia, E. Morallón, D. C. Amorós and Á. L. Solano, “Preparation of thin silicalite-1 layers on carbon materials by electrochemical methods,” *Micropor. Mesopor. Mater.*, 66 [2-3] 331-340 (2003).
 35. N. Kuanchertchoo, R. Suwanpreedee, S. Kulprathipanja, P. Aungkavattana, D. Atong, K. Hemra, T. Rirksomboon and S. Wongkasemjit, “Effect of synthesis parameters on zeolite membrane formation and performance by microwave technique,” *Appl. Organometal. Chem.*, 21 841-848 (2007).
 36. X. Xu., Y. Bao, C. Song, W. Yang, J. Liu, and L. Lin, “Synthesis, characterization and single gas permeation properties of NaA zeolite membrane,” *J. Membr. Sci.*, 249 [1-2] 51-64 (2005).
 37. T. Kyotani, T. Mizuno, Y. Katakura, S. Kakui, N. Shimotsuma, J. Saito, and T. Nakane, “Characterization of tubular zeolite NaA membranes prepared from clear solutions by FTIR-ATR, GIXRD and FIB-TEM-SEM,” *J. Membr. Sci.*, 296 [1- 2] 162-170 (2007).
 38. M. Abdollahi, S.N. Ashrafizadeh, and A. Malekpour, “Preparation of zeolite ZSM-5 membrane by electrophoretic deposition method,” *Micropor. Mesopor. Mater.*, 106 [1-3] 192-200 (2007).
 39. S. Nair, and M. Tsapatsis, Synthesis and properties of zeolite membranes, In Averbach, S and Dutta, P (Eds.) *Handbook of zeolite science and technology*, New York, Marcel Dekker, 875 (1993).
 40. E.A. Tsokanis and R.W. Thompson, “Further investigations of nucleation by initial breeding in the Al-free NH₄-ZSM-5 system,” *Zeolite*, 12 [4] 369-373 (1992).
 41. L. Gora and R.W. Thompson, “Controlled addition of aged mother liquor to zeolite NaA synthesis solutions,” *Zeolite*, 18 [2-3] 132-141 (1997).
 42. R. Szotak, *Handbook of molecular sieve*, Van Nostrand Reinhold, New York, (1992).


43. A. Tavolaro and P. Tavolaro, "LTA zeolite composite membrane preparation, characterization and application in a zeolitic membrane reactor," *Catal. Commun.*, 8 [5] 789-794 (2007).

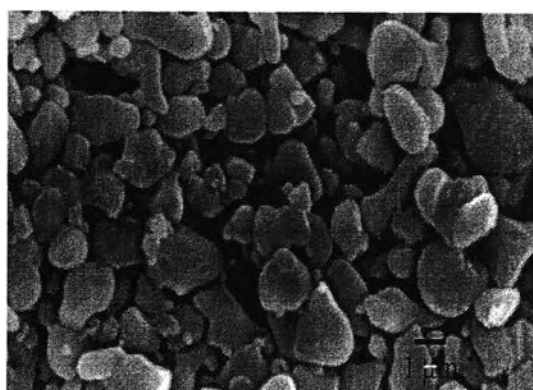


a)

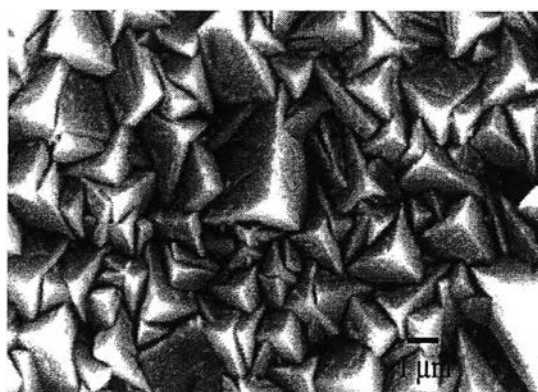


b)

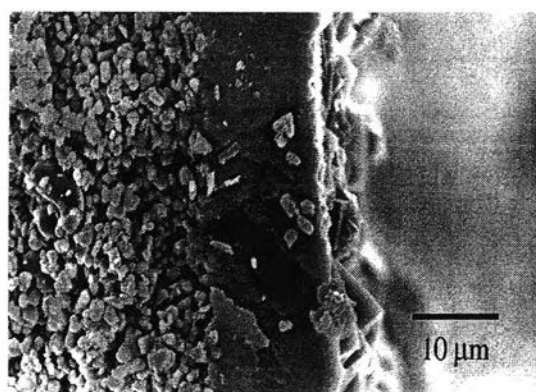

c)

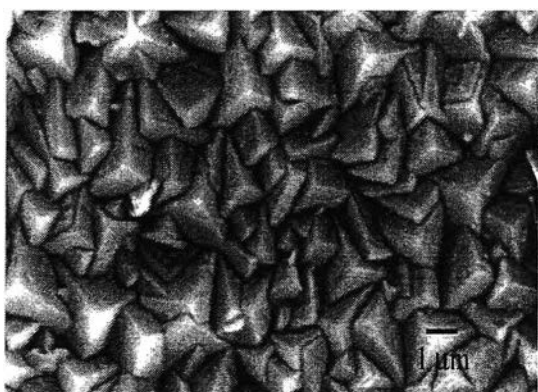

e)

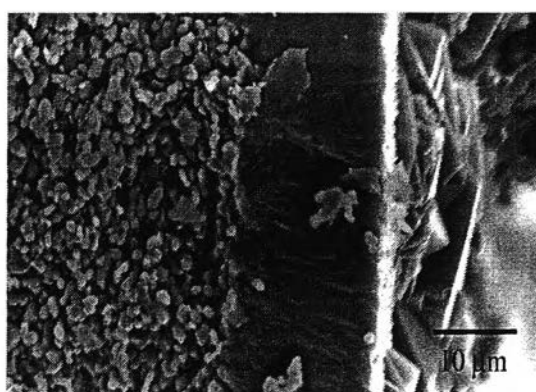

f)

Figure 6.1 SEM micrographs of a) α -Al₂O₃ support, b) and c) NaA zeolite membrane prepared by hydrothermal synthesis method and, d) and e) by electrophoretic technique.

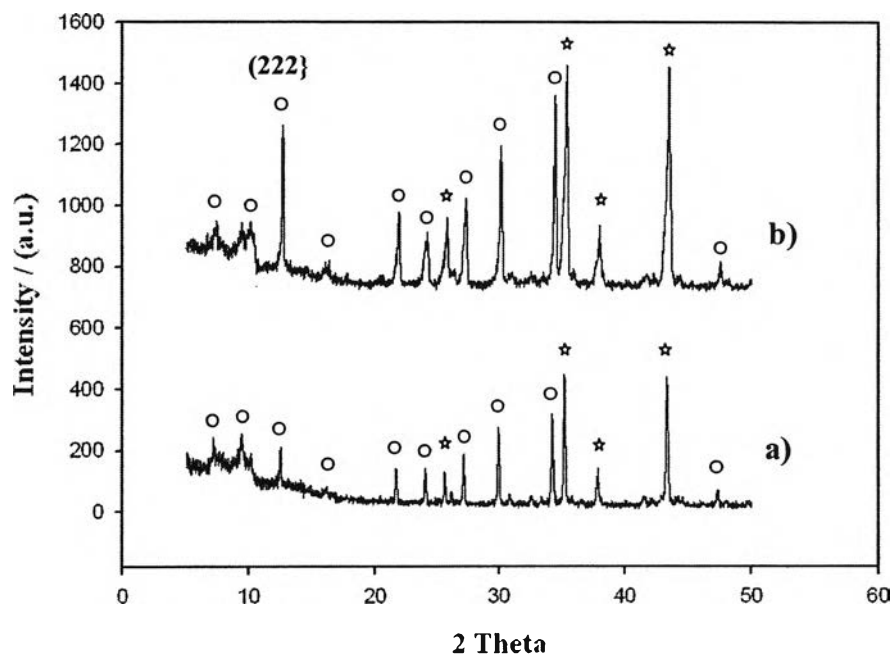


Figure 6.2 XRD pattern of the as-synthesized membrane of 2 min seeding on porous α - Al_2O_3 support before crystallizing by: a) hydrothermal method; b) electrophoretic technique; 1 V. (*) alumina substrate; (o) NaA zeolite.

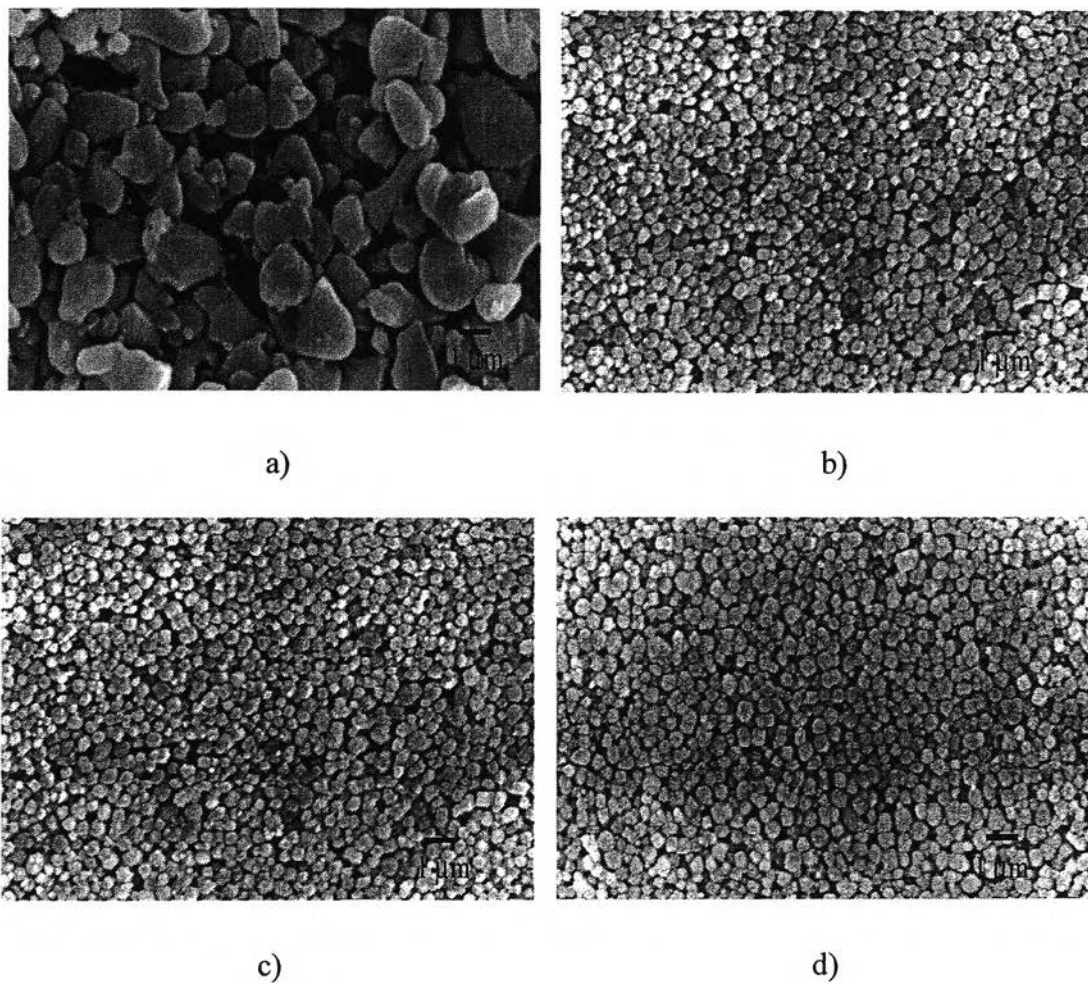


Figure 6.3 SEM micrographs of: a) α - Al_2O_3 substrate; and b), c) and d) NaA crystal seed (7 g/l) seeded by vacuum seeding on the α - Al_2O_3 substrate using 1.5, 2, and 3 min., respectively.

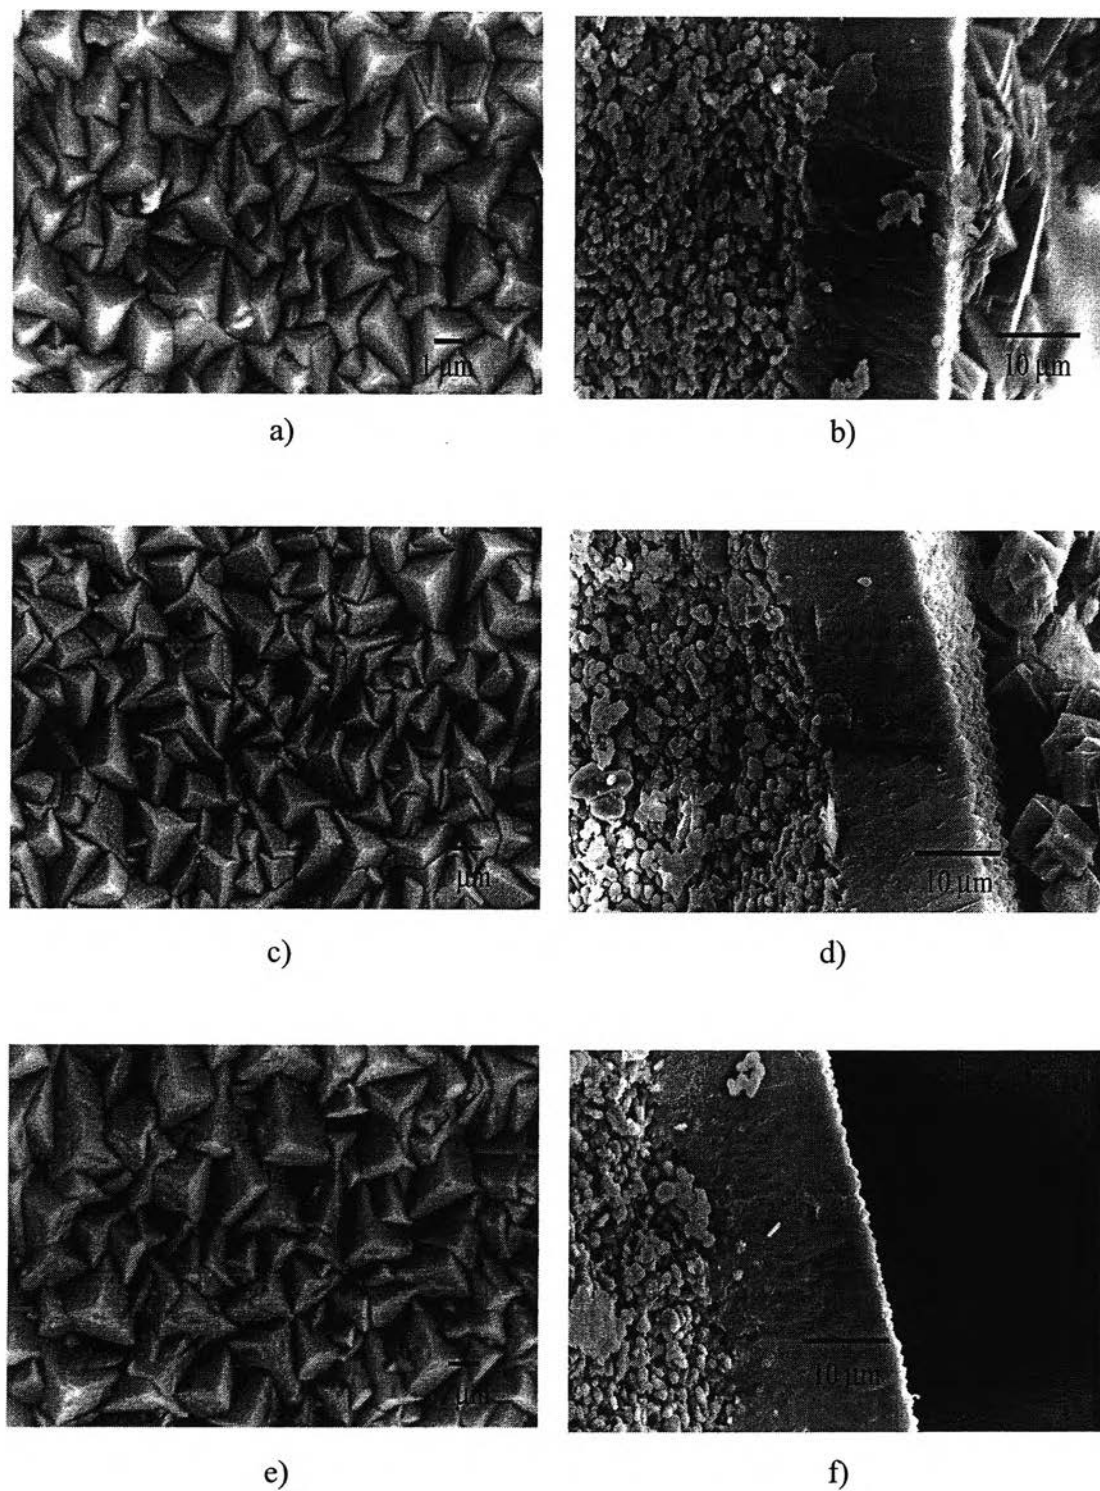


Figure 6.4 SEM micrographs of NaA zeolite membrane synthesized on substrate using a seed concentration of 7 g/l with seeding times of a) and b) 1.5 min., c) and d) 2 min, and e) and f) 3 min., under 333 K and electric field 2 V.

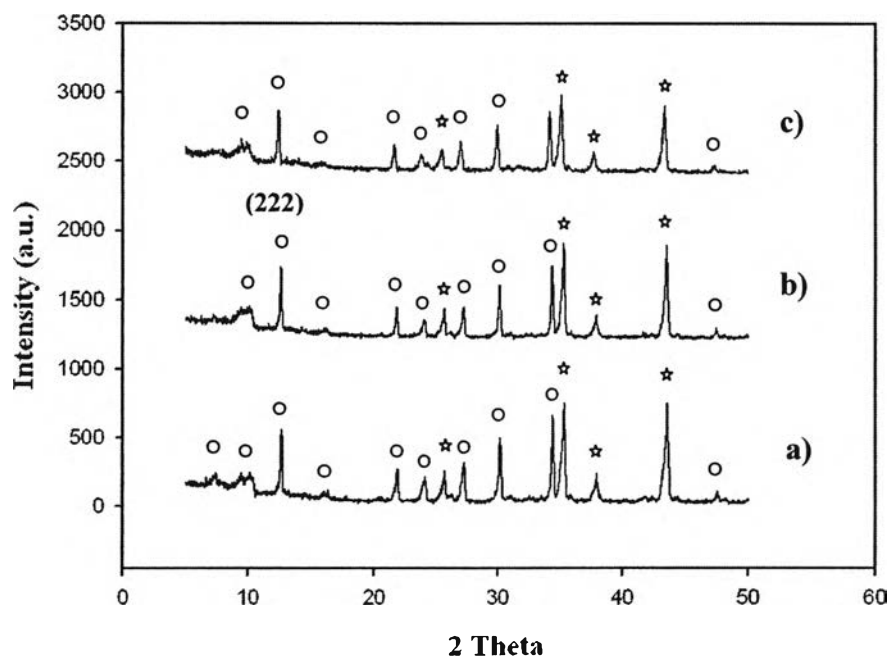


Figure 6.5 XRD pattern of NaA zeolite membrane synthesized on substrate using a seed concentration of 7 g/l with seeding times of a) and b) 1.5 min., c) and d) 2 min, and e) and f) 3 min., under 333 K and electric field 2 V. (*) alumina substrate; (o) NaA zeolite.

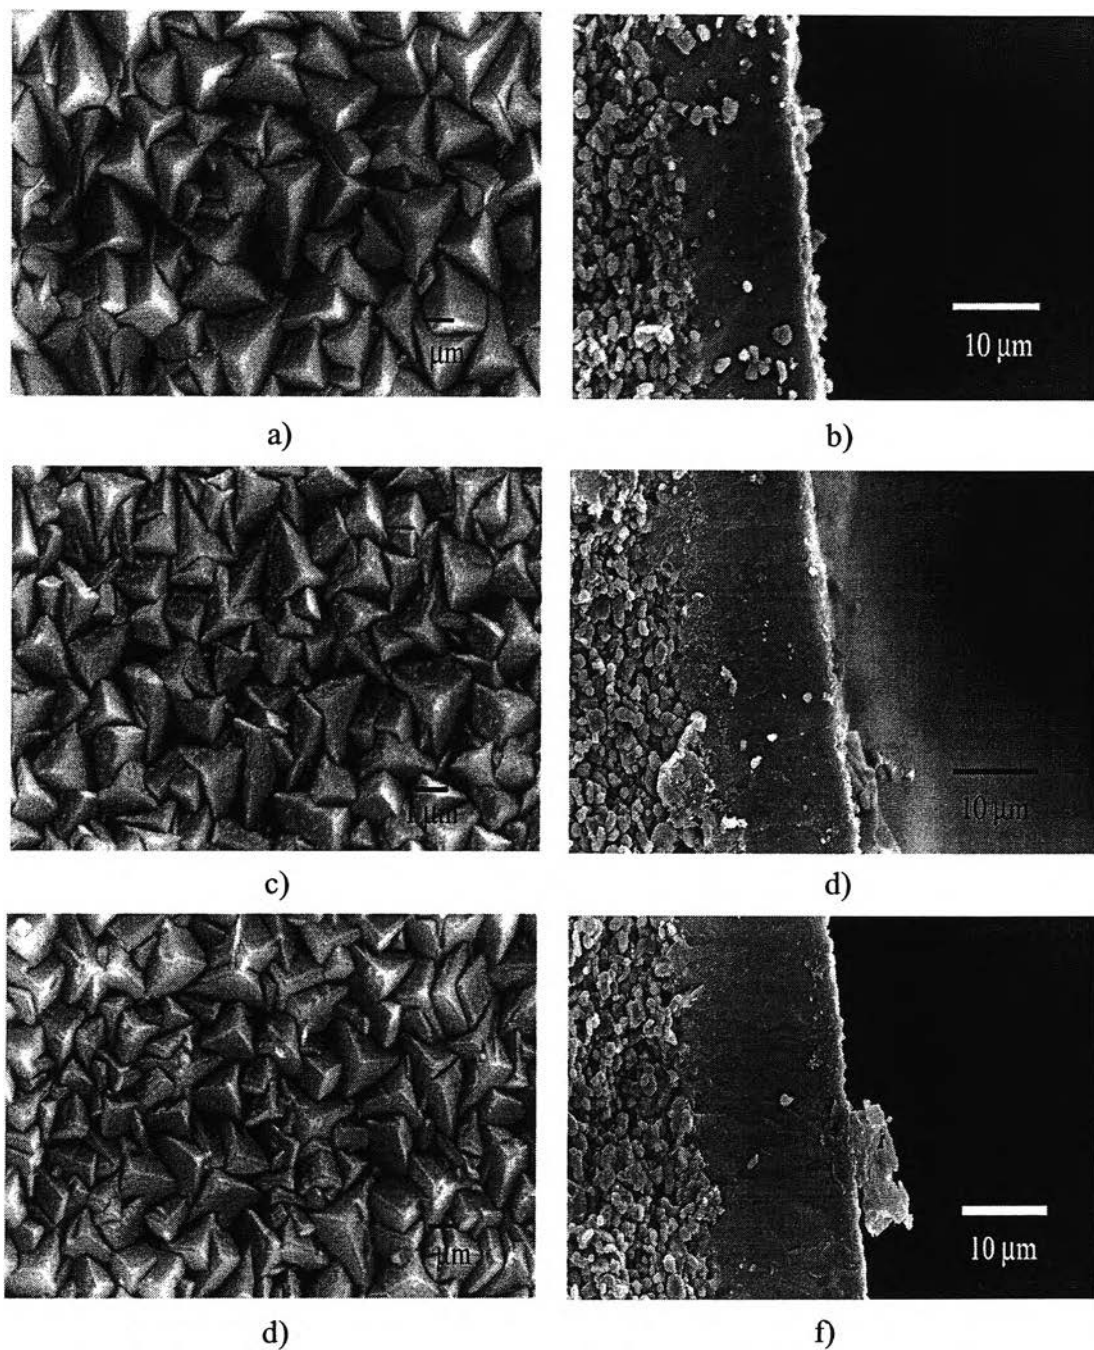


Figure 6.6 SEM micrographs of NaA zeolite membrane synthesized on Al_2O_3 support using a seed concentration of 7 g/l with a seeding time of 1.5 min and varying the electric field: a) and b) 1.0 V; c) and d) 1.5 V; and e) and f) 2 V.

Table 6.1 Pervaporation properties of as-synthesized NaA zeolite membrane using different seeding times parallel to several electrical potentials

Conditions		Membrane performance		
Electrical potentials (V)	Seeding time (min)	Zeolite layer (μm)	Flux ($\text{kg}/\text{m}^2 \cdot \text{h}$)	Separation factor
0	1.5	11-12	1	90.18
	2	12-13	0.74	>10,000
	3	14-15	0.95	208
1.0	1.5	13-14	0.98	432.31
	2	13-14	0.95	109.38
	3	16-17	0.80	75.15
1.5	1.5	16-17	0.74	2973.12
	2	18-19	0.75	324.58
	3	19-20	0.70	97.49
2.0	1.5	17-18	0.61	>10,000
	2	19-20	0.81	844.64
	3	20-21	1.2	633.92