


REFERENCES

1. Clark, C., Meardon, K., and Russell, D. Scrap tire technology and markets. U.S. Environmental Protection Agency: Noyes data, 1993.
2. Bank of Thailand. Tire industry. Trade of economic and industrial in Thailand. 1988-1995.
3. Lemieux, P.M., and Ryan, J.V. Characterization of air pollutants emitted from a simulated scrap tire fire. AIR & WASTE 43 (August 1993): 1106-1115.
4. Williams, P.T., Besler, S., and Taylor, D.T. The pyrolysis of scrap automotive tyres : The influence of temperature and heating rate on product composition. Fuel 69 (December 1996): 1474-1482.
5. Sponagel, P., and Kautschukindustrie, W.D. Tires. Ullmann's Encyclopedia of Industrial Chemistry A 27: 83-94.
6. Teng, H., Serio, M.A., Wojtowicz, M.A., Bassilakis, R., and Solomon, P.R. Reprocessing of used tires into activated carbon and other products. Ind. Eng. Chem. Res. 34 (1995): 3102-3111.
7. Customs Department, Finance Ministry. Imports and exports statistics of activated carbon. Foreign trade statistics of Thailand. 1988-1998.
8. Allport, H.B. Activated carbon. Encyclopedia of Science & Technology 7 (1992): 102.
9. Gerhartz, H., Yamamoto, Y.S., and Campbell, F.T. Activated carbon. Ullmann's Encyclopedia of Industrial Chemistry A 5 (1986): 124-140.
10. Hassler, J.W. Purification with activated carbon. New York: Mercei Dekker, 1974.
11. Hassler, J.W. Activated carbon. London: Leonard Hill, 1967.
12. Susek, M., and Cerry, S. Active carbon: manufacture, properties and application. Amsterdam: Elsevier, 1970.
13. Dammberg, E.M., Paquin, L., and Gwinnell, H. Carbon. Encyclopedia of Chemical Technology 4 (1992): 1040.

14. Jankowska, H., Swiatkowski, A., and Choma, J. Active carbon. Warsaw: Ellis Horwood, 1991.
15. Philip, C.A., and Girgis, B.S. Adsorption characteristics of microporous carbons from apricot stone activated by phosphoric acid. J. Chem. Tech. Biotechnol. 67(1996): 248-254.
16. Bansal, R.C., Donnet, J.B., and Stoeckli, F. Active carbon. New York: Marcel Dekker, 1988.
17. Satterfield, C.N. Heterogeneous catalysis in industrial practice. New York: McGRAW-HILL, 1991.
18. Torikai, N., Meguro, T., Nakamura, Y. Pore size distribution of activated carbon made from tires which contain carbon blacks differing in particle size. Nippon Kagaku Kaishi II (1979): 1604.
19. Ogasawara, S., Kuroda, M., and Wakao, N. Preparation of activated carbon by thermal decomposition of used automotive tires. Ind. Eng. Chem. Res. 26 (1987): 2552-2556.
20. Merchant, A.A., and Petrich, M.A. Pyrolysis of scrap tires and conversion of chars to activated carbon. AIChE J 39, No.8 (1993): 1370-1376.
21. Tancredi, N., Cordero, T., Mirasol, J.R., and Rodriguez, J.J. Activated carbons from Uruguayan eucalyptus wood. Fuel 75, No.15 (1996): 1701-1706.
22. Ratikorn Isarasaene. Production of activated carbon from used tires by superheat steam activation. Master's Thesis, Department of Chemical Technology, Graduate School, Chulalongkorn University, 1996.
23. Sai, P.M., Ahmed, J., and Krishnaiah, K. Production of activated carbon from coconut shell char in a fluidized bed reactor. Ind. Eng. Chem. Res. 36 (1997): 3625-3630.
24. Thailand Industrial Standard Institute, Industry Ministry. Activated carbon. Standard of commercial activated carbon TIS 900-1989: 1-10.
25. American Standard of Testing Material. Standard test method for chemical analysis of wood charcoal. Annual book of ASTM standards D 1762-84 (Reapproved 1995)⁶¹: 281-282.

26. American Standard of Testing Material. Standard test method for moisture in activated carbon. Annual book of ASTM standards D 2867-95: 500-502.
27. American Standard of Testing Material. Standard test method for total ash content of activated carbon. Annual book of ASTM standards D 2866-94: 498-499.
28. American Standard of Testing Material. Standard test method for apparent density of activated carbon. Annual book of ASTM standards D 2854-89 (Reapproved 1993)⁸¹: 491-493.
29. American Standard of Testing Material. Standard test method for determination of iodine number of activated carbon. Annual book of ASTM standards D 4607-94: 542-545.
30. Japanese Standard Association. Standard testing method of methylene blue number of activated carbon. Japanese industrial standard test method for activated carbon. JIS K 1470-1991.
31. American Standard of Testing Material. Standard test methods for carbon black-Surface area by multipoint B.E.T. nitrogen adsorption. Annual book of ASTM standards D 4820-96a⁸¹: 756-762.

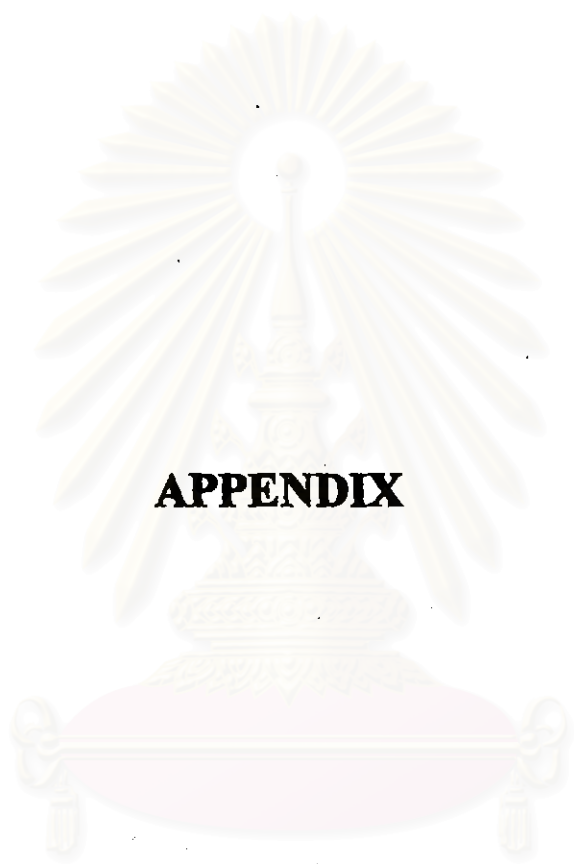

APPENDIX

สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย



Appendix A

Table A.1 Properties of commercial activated carbons (TIS 900-1989).

Table A.2 Properties of commercial powdered activated carbon.

Table A.3 Properties of commercial granular activated carbon.

สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย

Table A.1 Properties of commercial activated carbons limit by TIS 900-1989.

Types	Size	% Moisture	BD (cm^3/g)	IA (mg/g)
Powdered activated carbon	< 150 μm	-	0.20 - 0.75	> 600
Granular activated carbon	> 150 μm	< 8	> 0.36	> 600

Table A.2 Properties of commercial powdered activated carbon.

Trade names	Raw material	Ash (%)	BD (g/cm^3)	S_{BET} (m^2/g)	MB (mg/g)	IA (mg/g)
UDP CHEMICAL (Thailand)						
MDP1-7325	Coconut shell	3	0.40-0.55	1200-1300	230	1050
PN3	-	8	0.46	-	-	800
Taiko PKW	Sawdust	2	-	-	-	-
Shirasagi KW	Sawdust	3	-	-	-	-
Nuchar SA	-	3-5	0.37-0.40	-	-	900
Nuchar SN	-	3-5	0.37-0.40	-	-	900
PITTSBURGH ACTIVATED CARBONS						
RB	Bituminous	23	-	1250-1400	-	1200
RC	Bituminous	21	-	1100-1300	-	1100
BL	Bituminous	8.5	-	1000-1100	300	1000
C	Bituminous	14	-	1000-1100	-	900
GW	Bituminous	12	-	1000-1100	180	700

Table A.3 Properties of commercial granular activated carbon.

Trade names	Raw material	Ash (%)	BD (g/cm ³)	S _{BET} (m ² /g)	MB (mg/g)	IA (mg/g)
UDP CHEMICAL (Thailand)						
MD-G 7746	Coconut shell	3	0.40-0.45	1100-1200	200	1050
MD-W 7830	Coconut shell	3	0.50-0.55	1150-1250	220	1050
SUTCLIFFE SPEAKMAN (England)						
	Coal	6-16	0.40-0.56	600-1250	-	-
	Coconut shell	1-4	0.40-0.59	700-1500	-	-
NORIT ACTIVATED CARBON						
PK1-3	Peat	6	-	800	-	800
Nuchar 681	Bituminous	-	0.43-0.46	1100	-	-
AG-5	-	6	0.38-0.45	900-1000	-	-
PJAC (Japan)						
CG-4X10	Coconut shell	5	0.42-0.47	1200-1300	170	1050
CG-6X8	Coconut shell	5	0.42-0.47	1200-1300	170	1100
CW-8X30	Coconut shell	5	0.45-0.50	1050-1150	170	1050
SYBRON	Bituminous	-	0.50-0.55	900	220	900
IONAC P-50 (USA)						
Calgon Filtrasorb 100-200	Bituminous	-	-	850-900	-	850
CALGON SGL	Bituminous	10	0.48	950-1050	-	900
PITTSBURGH ACTIVATED CARBONS						
<i>vapor phase</i>						
- PCB	Bituminous	4.0	0.44	-	-	1200
- BPL	Bituminous	8.0	0.48	-	-	1050
<i>liquid phase</i>						
- CAL	Bituminous	8.5	0.44	-	-	1000
- OL	Bituminous	8.0	0.44	-	-	1000
- SGL	Bituminous	8.0	0.48	-	-	900
Nuchar WV-G	-	-	0.43-0.46	1100	-	1050

Appendix B

Appendix B.1 Standard Test Method for Chemical analysis of Wood Charcoal (ASTM D 1762-84).

Appendix B.2 Standard Test Method for Apparent Density of Activated Carbon (ASTM D 2884-89).

Appendix B.3 Standard Test Method for Moisture in Activated Carbon (ASTM D 2867-95).

Appendix B.4 Standard Test Method for Total Ash Content of Activated Carbon (ASTM D 2866-94).

Appendix B.5 Standard Test Method for Determination of Iodine Number of Activated Carbon (ASTM D 4607-94).

Appendix B.6 Standard testing method of Methylene blue number of Activated Carbon (JIS K 1470-1991).

Appendix B.7 Standard Test Methods for Carbon Black-Surface area by multipoint B.E.T. Nitrogen Adsorption (ASTM D 4820-96a).

จุฬาลงกรณ์มหาวิทยาลัย

Appendix B.1

Standard Test Method for Chemical analysis of Wood Charcoal (ASTM D 1762-84)

This test method covers the determination of moisture, volatile matter, and ash in charcoal made from wood. The sample is ground in a specified manner and the moisture determined as loss in weight in a drying oven at 105°C. Volatile matter is determined as loss in weight at 950°C under specified conditions. Ash is determined as the residue after burning to constant weight at 750°C.

Procedure (for Activated carbon Passing A No. 50 Sieve)

1. Make duplicate determinations.

2. **Moisture** Heat the muffle furnace to 750°C and place previously ignited porcelain crucible (*Note1*) and covers in the furnace for 10 min. Cool the crucibles in a desiccator for 1 hr. Weigh the crucibles and add to each approximately 1 g, weighed to the nearest 0.1 mg, of the ground sample. Place the samples in the oven at 105°C for 2 hr. Place the dried samples in a desiccator for 1 hr and weigh (*Note2*).

Note1 In practice, a crucible from a previous determination is used

Note2 The sample shall be considered oven-dry when, the decrease in weight of consecutive weightings is 0.0005 g or less. Succeeding drying periods shall be not less than 1 hr.

3. **Volatile Matter** Heat the muffle furnace to 950°C. Preheat the crucibles used for the moisture determination, with lids in place and containing the sample, as follows: with the furnace door open, for 2 min on the outer ledge of the furnace (300°C) and then for 3 min on the edge of the furnace (500°C) (*Note3*). Then move the samples to the rear of the furnace for 6 min with the muffle door closed. Watch the samples through a small peep-hole in the muffle door. If sparking occurs, results will be in error (*Note4*). Cool the samples in a desiccator for 1 hr and weigh.

Note3 Individual nichrome wire baskets to hold the crucibles are convenient.

Note4 If the sparking sample does not check the results of its nonsparking duplicate within $\pm 0.5\%$, the analysis shall be repeated.

4. *Ash* Place the lids and the uncovered crucible used for the volatile matter determination, and containing the sample in the muffle furnace at 750°C for 6 hr. Cool the crucibles with lids in place in a desiccator for 1 hr and weigh. Repeat burning of the sample until a succeeding 1 hr period of heating results in a loss of less than 0.0005 g.

Calculation

1. Calculate the percentage of moisture in the sample as follows:

Calculate the moisture content as follows:

$$\text{Moisture, \%} = [(A - B) / A] \times 100$$

where:

A = grams of air-dry sample used, and

B = grams of sample after drying at 105°C .

2. Calculate the percentage of volatile matter content in the sample as follows:

$$\text{Volatile matter, \%} = [(B - C) / B] \times 100$$

where:

C = grams of sample after drying at 950°C .

3. Calculate the percentage of ash in the sample as follows:

$$\text{Ash, \%} = (D / B) \times 100$$

where:

D = grams of residue.

Appendix B.2

Standard Test Method for Apparent Density of Activated Carbon (ASTM D 2884-89)

This test method covers the determination of the apparent density (bulk density) of granular activated carbon. It is determined on granular sample by measuring the volume packed by a free fall from a vibrating feeder into a 10 mL graduated cylinder and weighing the known volume. For purposes of this test method, granular activated carbon is defined as a minimum of 90% being larger than 80 mesh.

Procedure

1. Dry an adequate sample of the carbon to be tested to constant weight at $150 \pm 5^\circ\text{C}$.
2. Carefully place a representative sample of the activated carbon into the feed funnel so that the material does not prematurely flow into the graduated cylinder.
3. Fill the cylinder at a uniform rate up to the 10 mL mark.
4. Transfer the contents from the cylinder to a balance pan and weigh to the nearest 0.1 g.

Calculation

Calculate the bulk density as follows :

$$\text{Bulk density, g/mL} = \text{weight of activated carbon}/10$$

Appendix B.3

Standard Test Method for Moisture in Activated Carbon (ASTM D 2867-95)

These test methods for the determination of the moisture content of activated carbon, for this work used the oven-drying method. The oven-drying method is used when water is the only volatile material present and is in significant quantities, and the activated carbon is not heat-sensitive (some activated carbons can ignite spontaneously at temperatures as low as 150°C). A sample of carbon is put into dry, closed capsule (of known weight) and weighed accurately. The capsule is opened and placed with the lid in a preheated oven. The sample is dried to constant weight then removed from the oven and with the capsule closed, cooled to ambient temperature. The closed capsule is weighed again accurately. The weight loss is expressed as a percentage of the weight of the original sample.

Procedure (for Activated carbon Passing A No. 50 Sieve)

1. Dip out with a spoon or spatula from the sample bottle a 1 to 2 g representation sample. Put this into a predried tared capsule with lid, close and weigh at once to the nearest 0.5 mg. The depth of the carbon in the capsule must not exceed 1.25 cm.
2. Remove the cover and place the capsule and cover in a preheated forced circulation oven (at 145 to 155 °C). Close the oven and dry to constant weight (3 hr normally sufficient). Open the oven and cover the capsules quickly. Cool in a desiccator to ambient temperature and weigh.

Calculation

Calculate the moisture content as follows:

$$\text{Moisture, weight \%} = [(C - D) / (C - B)] \times 100$$

where:

- B* = weight of capsule with cover, g
C = weight of capsule with cover plus original sample, g, and
D = weight of capsule with cover plus dried sample, g.

Appendix B.4

Standard Test Method for Total Ash Content of Activated Carbon (ASTM D 2866-94)

This test method describes a procedure for the determination of total ash content of activated carbon. An accurately weighed sample of dried activated carbon is placed in a controlled-temperature muffle furnace for a period of several hours. When constant weight has been achieved, the crucible is cooled to ambient temperature in a desiccator and reweighed. The weight of the ashed carbon is expressed as a percentage of the weight of the original carbon sample.

Procedure

1. Ignite the crucible in the muffle furnace at 650 ± 25 °C for 1 hr. Place the crucible in the desiccator. Cool to room temperature and weigh to the nearest 0.1 mg.
2. Dry an adequate sample of activated carbon to constant weight at 150 ± 5 °C (3 hr is usually sufficient).
3. Weigh out to the nearest 0.1 mg sufficient dried activated carbon, so that the estimated amount of ash will be 0.1 g, into the ignited crucible and place the crucible in the furnace at 650 ± 25 °C. Ashing will require from 3 to 16 hr, depending on the size and type of activated carbon. Ashing can be considered complete when constant weight is achieved.
4. Place the crucible in the desiccator and allow to cool to room temperature. After the sample has cooled in the desiccator, admit air slowly to avoid loss of ash from the crucible. weigh to the nearest 0.1 mg.

Calculation

Calculate the ash content as follows:

$$\text{Total ash, \%} = [(D - B) / (C - B)] \times 100$$

where:

- B = weight of crucible, g,
- C = weight of crucible plus original sample, g, and
- D = weight of crucible plus ashed sample, g.

Appendix B.5

Standard Test Method for Determination of Iodine Number of Activated Carbon (ASTM D 4607-94)

This test method covers the determination of the relative activation level of unused of reactivated carbons by adsorption of iodine from aqueous solution. The amount of iodine absorbed (in milligrams) by 1 g of carbon using test conditions listed herein is called the iodine number.

This test method is based upon a three-point adsorption isotherm. A standard iodine solution is treated with three different weights of activated carbon under specified conditions. The carbon treated solution are filtered to separate the carbon from the treated iodine solution (filtrate). Iodine remaining in the filtrate is measured by titration. The amount of iodine removed per gram of carbon is determined for each carbon dosage and the resulting data used to plot an adsorption isotherm. The amount of iodine adsorbed (in milligrams) per gram of carbon at a residual iodine concentration of 0.02 *N* is reported as the iodine number.

1. Preparation of solutions

1.1 *Hydrochloric Acid Solution* (5 % by weight). Add 70 mL of concentrated hydrochloric acid to 550 mL of distilled water and mix well. A graduated cylinder may be used for measurement of volume.

1.2 *Sodium Thiosulfate* (0.100 *N*). Dissolve 24.820 g of sodium thiosulfate in approximately 75 ± 25 mL of freshly boiled distilled water. Add 0.10 ± 0.01 g of sodium carbonate to minimize bacterial decomposition of the thiosulfate solution. Quantitatively transfer the mixture to a 1 L volumetric flask and dilute to the mark. Allow the solution to stand at least 4 days before standardizing. The solution should be stored in an amber bottle.

1.3 *Standard Iodine Solution* (0.100 ± 0.001 *N*). Weigh 12.700 g of iodine and 19.100 g of potassium iodine (KI) into a beaker. Mix the dry iodine and potassium

iodine. Add 2 to 5 mL of water to the beaker and stir well. Continue adding small increments of water (approximately 5 mL each) while stirring until the total volume is 50 to 60 mL. Allow the solution into stand a minimum of 4 hr to ensure that all crystals are thoroughly dissolved. Occasional stirring during this 4 hr period will aid in the dissolution. Quantitatively transfer to a 1 L volumetric flask and fill to the mark with distilled water. It is important that the standard iodine solution has an iodine-to-iodine weight ratio of 1.5 to 1. Store the solution in an amber bottle.

1.4 *Potassium Iodate Solution (0.1000 N)*. Dry 4 or more grams of primary standard grade potassium iodate (KIO_3) at $110 \pm 5^\circ\text{C}$ for 2 hr and cool to room temperature in a desiccator. Dissolve 3.5667 ± 0.1 mg of the dry potassium iodate in about 100 mL of distilled water. Quantitatively transfer to a 1-L volumetric flask and fill to the mark with distilled water. Mix thoroughly and store in a glass-stoppered bottle.

1.5 *Starch Solution*. Mix 1.0 ± 0.5 g of starch with 5 to 10 mL of cold water to make a paste. Add an additional 25 ± 5 mL of water while stirring to the starch paste. Pour the mixture, while stirring, into 1 L of boiling water and boil for 4 to 5 min. This solution should be made fresh daily.

2. Standardization of solutions

2.1 *Standardization of 0.100 N Sodium Thiosulfate*. Pipet 25.0 mL of potassium iodate (KIO_3) solution from 1.2 into a 250-mL titration (or wide-mouthed Erlenmeyer) flask. Add 2.00 ± 0.01 g of potassium iodide (KI) to the flask and shake the flask to dissolve the potassium iodide crystals. Pipet 5.0 mL of concentrated hydrochloric acid into the flask. Titrated the free iodine with sodium thiosulfate solution until a light yellow color is observed in the flask. Add a few drops of starch indicator (1.5) and continue the titration dropwise until one drop produces a colorless solution. Determine sodium thiosulfate normality as follows:

$$N_t = (P \cdot R) / S$$

where :

N_t = sodium thiosulfate, N_s

- P = potassium iodate, mL,
 R = potassium iodate, N , and
 S = sodium thiosulfate, mL.

The titration step should be done in triplicate and the normality results averaged. Additional replications should be done if the range of values exceeds 0.003 N .

2.2 Standardization of 0.100 ± 0.001 N Iodine solution. Pipet 25.0 mL of iodine solution (1.3) into a 250-mL wide mouthed Erlenmeyer flask. Tritrate with standardized sodium thiosulfate (2.1) until the iodine solution is a light yellow color. Add a few drops of starch indicator (1.5) and continue the titration dropwise until one drop produces a colorless solution. Determine iodine solution normality as follows:

$$N_2 = (S \cdot N_1) / I$$

where:

- N_2 = iodine, N ,
 S = sodium thiosulfate, mL,
 N_1 = sodium thiosulfate, N , and
 I = iodine, mL.

The titration step should be done in triplicate and the normality results averaged. Additional replications should be done if the range of values exceeds 0.003 N . The iodine solution concentration must be 0.100 ± 0.001 N . If this requirement is not met, repeat 1.3 and 2.2.

3. Procedure

3.1 The procedure applies to either powdered or granular activated carbon. When granular carbon is to be tested, grind a representative sample of carbon until 60 wt % (or more will pass through a 325-mesh screen) and 95 wt% or more will pass through a 100-mesh screen (U.S. sieve series, see specification E 11). Carbon received in the

powdered form may need additional grinding to meet the particle size requirement given above.

3.2 Dry the ground carbon from 3.1 in accordance with Test Method D 2867. Cool the dry carbon to room temperature in a desiccator.

3.3 Determination of iodine number requires an estimation of three carbon dosages. Section 4 and Table B.5.1 describes how to estimate the carbon dosages to be used. After estimating carbon dosages, weigh three appropriate amounts of dry carbon to the nearest milligram. Transfer each weighed sample of carbon to a clean, dry 250-mL Erlenmeyer flask equipped with a ground glass stopper.

3.4 Pipet 10.0 mL of 5 wt% hydrochloric acid solution into each flask containing carbon. Stopper each flask and swirl gently until the carbon is completely wetted. Loosen the stoppers to vent the flasks, place on a hot plate in a fume hood, and bring the contents to a boil. Allow to boil gently for 30 ± 2 s to remove any sulfur which may interfere with the test results. Remove the flasks from hot plate and cool to room temperature.

3.5 Pipet 100.0 mL of 0.100 *N* iodine solution into each flask. Standardize the solution just prior to use. Stagger the addition of iodine to the three flasks so that no delays are encountered in handling. Immediately stopper the flasks, and shake the contents vigorously for 30 ± 1 s. Quickly filter each mixture by gravity through one sheet of folded filter paper (Whatman No. 2V or equivalent) into a beaker. Filtration equipment must be prepared in advance so no delay is encountered in filtering the samples.

3.6 For each filtrate, use the first 20 to 30 mL to rinse a pipet. Discard the rinse portions. Use clean beakers to collect the remaining filtrates. Mix each filtrate by swirling the beaker and pipet 50.0 mL of each filtrate into a clean 250-mL Erlenmeyer flask. Titrate each filtrate with standardized 0.100 *N* sodium thiosulfate solution until the solution is a pale yellow. Add 2 mL of the starch indicator solution and continue the titration with sodium thiosulfate until one drop produces a colorless solution. Record the volume of sodium thiosulfate used.

4. Calculation

4.1 The capacity of carbon for any adsorbate is dependent upon the concentration of the adsorbate in solution. The concentrations of the standard iodine solution and filtrates must be specified or known. This is necessary to determine an appropriate carbon weight to produce final concentrations agreeing with the definition of iodine number. The amount of carbon sample to be used in the determination is governed by the activity of the carbon. If filtrate normalities (C) are not within the range of $0.008 N$ to $0.040 N$, repeat the procedure using different carbon weights.

4.2 Two calculations are required for each carbon dosage, as X/M and C .

4.2.1 To calculate the value of X/M , first derive the following values:

$$A = (N_2) (12693.0)$$

where:

N_2 = iodine, N (from 2.2).

$$B = (N_1) (126.93)$$

where:

N_1 = sodium thiosulfate, N (from 2.1)

$$DF = (I + H) / F$$

where:

DF = dilution factor,

I = iodine, mL (from 2.2),

H = 5% hydrochloric acid used, mL, and

F = filtrate, mL.

For example, if 10 mL of HCl and 50 mL of filtrate are used: $DF = (100 + 10) / 50 = 2.2$.

4.2.1.1 Calculate the value of X/M as follows:

$$X/M = [A - (DF) (B) (S)] / M$$

where:

X/M = iodine absorbed per gram of carbon, mg/g,

S = sodium thiosulfate, N , and

M = carbon used, g.

4.2.2 Calculate the value of C as follows:

$$C = (N_1 \cdot S) / F$$

where:

C = residual filtrate, N ,

N_1 = sodium thiosulfate, mL, and

F = filtrate, mL.

4.3 Using logarithmic paper, plot X/M (as the ordinate) versus C (as the abscissa) for each of the three carbon dosages. Calculate the least squares fit for the three points and plot. The iodine number is the X/M value at a residual iodine concentration (C) of 0.02 N . The regression coefficient for the least squares fit should be greater than 0.995.

จุฬาลงกรณ์มหาวิทยาลัย

4.4 Carbon dosage may be estimated as follows:

$$M = [A - (DF) (C) (126.93) (50)] / E$$

where:

M = carbon, g,

A = $(N_2) (12693.0)$,

DF = dilution factor (see 4.2.1)

C = residual iodine, and

E = estimated iodine number of the carbon.

Three carbon dosage are calculated using three values of C (usually 0.01, 0.02, and 0.03).

Table B.5.1 Find M for calculation iodine number by using ASTM D4607-86.

IA	M			IA	M		
	C = 0.01	C = 0.02	C = 0.03		C = 0.01	C = 0.02	C = 0.03
300	3.766	3.300	2.835	1550	0.729	0.639	0.549
350	3.228	2.829	2.430	1600	0.706	0.619	0.531
400	2.824	2.475	2.126	1650	0.684	0.600	0.515
450	2.510	2.200	1.890	1700	0.664	0.582	0.500
500	2.259	1.980	1.701	1750	0.645	0.566	0.486
550	2.054	1.800	1.546	1800	0.628	0.550	0.472
600	1.883	1.650	1.417	1850	0.610	0.535	0.460
650	1.738	1.523	1.308	1900	0.594	0.521	0.447
700	1.614	1.414	1.215	1950	0.579	0.508	0.436
750	1.506	1.320	1.134	2000	0.565	0.495	0.425
800	1.412	1.237	1.063	2050	0.551	0.483	0.415
850	1.329	1.164	1.000	2100	0.538	0.471	0.405
900	1.255	1.100	0.945	2150	0.525	0.460	0.396
950	1.189	1.042	0.895	2200	0.513	0.450	0.386
1000	1.130	0.990	0.850	2250	0.502	0.440	0.378
1050	1.076	0.943	0.810	2300	0.491	0.430	0.370
1100	1.027	0.900	0.773	2350	0.481	0.421	0.362
1150	0.982	0.861	0.739	2400	0.471	0.412	0.354
1200	0.941	0.825	0.709	2450	0.461	0.404	0.347
1250	0.904	0.792	0.680	2500	0.452	0.396	0.340
1300	0.869	0.761	0.654	2550	0.443	0.388	0.333
1350	0.837	0.733	0.630	2600	0.434	0.381	0.327
1400	0.807	0.707	0.607	2650	0.426	0.374	0.321
1450	0.779	0.683	0.586	2700	0.418	0.367	0.315
1500	0.753	0.660	0.567	2750	0.411	0.360	0.309

Appendix B.6

Standard testing method of Methylene Blue Number of Activated Carbon (JIS K 1470-1991)

1. Preparation of solutions

1.1 *Potassium dihydrogen phosphate solution* - Dry of potassium dihydrogen phosphate (KH_2PO_4) in the oven at $110\text{-}120^\circ\text{C}$ for 2 hr and cool to room temperature in a desiccator. Dissolve 9.07 g of dry KH_2PO_4 with distilled water. Quantitatively transfer to a 1-L volumetric flask and fill to the mark with distilled water.

1.2 *Disodium hydrogen phosphate solution*- Dry of disodium hydrogen phosphate (Na_2HPO_4) in the oven at $110\text{-}120^\circ\text{C}$ for 2 hr and cool to room temperature in a desiccator. Dissolve 23.88 g of dry Na_2HPO_4 with distilled water. Quantitatively transfer to a 1-L volumetric flask and fill to the mark with distilled water.

1.3 *Buffer solution* - Mix 400 mL of 1.1 and 600 mL of 1.2 . The pH of this solution is approximately 7.

1.4 *Standard methylene blue solution* - Dry of methylene blue in the oven at $105 \pm 5^\circ\text{C}$ for 4 hr and cool to room temperature in a desiccator. Dissolve 1.2 g of dry methylene blue with buffer solution. Quantitatively transfer to a 1-L volumetric flask and fill to the mark with buffer solution.

2. Procedure

2.1 Dry of activated carbon at $150 \pm 5^\circ\text{C}$ (3 hr is usually sufficient).

2.2 Weigh the specified amount (note 1) of activated carbon to the nearest 1 mg, transfer to an Erlenmeyer flask with ground-in stopper 100 mL, and add methylene blue solution 25 mL.

2.3 Shake at room temperature using a shaker for 30 min.

2.4 Take methylene blue solution 10 mL into one mark volumetric flask 50 mL, and add buffer solution up to the marked line. Further, take its 5 mL into other one mark volumetric flask 500 mL, and add buffer solution up to the marked line. In this case the concentration of methylene blue solution is 0.24 mg/l.

2.5 Measure the absorbance at wavelength of 665 nm with contrasting to buffer solution.

Note 1 Weigh the sample by dividing into three stage degree so that the mass interval does not exceed 0.02 g corresponding to anticipated methylene blue adsorption performance to the sample 0.1 to 0.3 g.

3. Preparation of calibration curve

3.1 Take methylene blue solution 10 mL into one mark volumetric flask 50 mL, and add buffer solution up to the marked line. From this solution, take 5, 10, 25 and 50 mL into respective one mark volumetric flask 500 mL, and add buffer solution up to the marked line.

3.2 For these solution, prepare the relation curve between the concentration of methylene blue solution (0.24 to 2.4 mg/l) and the absorbance at 665 nm in wavelength and obtain from this the remaining concentration of methylene blue.

4. Calculation Using the remaining concentration of methylene blue obtain in 3, the methylene blue amount (mg/g) shall be calculated using the following formula.

$$Q = \frac{(1200-C) (25/1000)}{S}$$

where :

Q	=	Methylene blue adsorption amount (mg/g),
C	=	remaining concentration of methylene blue (mg/l),
S	=	mass of activated carbon (g) and
1200	=	concentration of methylene blue solution (mg/l).

5. Preparation of adsorption isotherm in methylene blue solution. Plot the remaining concentration of methylene blue solution obtained in 3 on the abscissa and the adsorption amount of methylene blue obtained using the calculation method of 4 on the ordinate of both logarithm graph and prepare the adsorption isotherm. From the adsorption isotherm obtain the methylene blue amount (mg/g) of sample when the remaining concentration of methylene blue as the methylene blue adsorption performance is 0.24 mg/L.

Appendix B.7

Standard Test Methods for Carbon Black-Surface area by multipoint B.E.T. Nitrogen Adsorption (ASTM D 4820-96a)

A carbon sample is placed in a known volume cell and evacuated to less than 5 millitorr of vacuum. Using the ideal gas equation, the volume of nitrogen required to give a predetermined relative pressure is calculated and dosed into the sample cell. Any additional nitrogen required to attain this relative pressure is due to adsorption by the carbon. Based on the volume of nitrogen adsorbed at various relative pressures, the surface area is calculated.

Theory of Test Method

The determination of surface area from the B.E.T. theory is a straight forward application of the B.E.T. equation :

$$\frac{1}{V [(P_0/P) - 1]} = \frac{1}{V_M C} + \frac{C - 1}{V_M C} \times \frac{P}{P_0}$$

where :

V = volume of nitrogen adsorbed, cm³,

P = pressure, kPa,

P₀ = saturation vapor pressure of nitrogen, kPa,

V_M = volume of nitrogen that covers one monomolecular layer, cm³, and

C = B.E.T. constant.

A plot of $1 / V [(P_0/P) - 1]$ versus P / P_0 will usually yield a straight line in the range 0.05 to 0.35. Solving the B.E.T. equation for V_M gives:

$$V_M = \frac{1}{M + B}$$

where:

M = slope of straight line, and

B = y-intercept.

Sample Preparation

1. Place a clean sample tube on the degassing station and heat at 150°C for 0.5 hr at a pressure below 2.7 Pa (20 μmHg). The insertion of a glass rod into the sample tube stem will reduce the void volume of the stem, thus improving testing precision.
2. Cool the sample tube to room temperature, then backfill, preferably with helium to atmospheric pressure. Place a stopper on the sample tube and weigh it to the nearest 0.0001 g and record as mass *A*.
3. For samples of unknown surface area, place approximately 0.1 g of carbon in the sample tube clean the sample tube stem with a pipe cleaner.
- 4 Place the sample tube containing the carbon on the degassing station and open the vacuum valve.
5. Place the heating mantle on the sample cell and heat at 150°C for 1 hr or longer to obtain and hold a pressure less than 2.7 Pa (20 μmHg).
6. Remove the heating mantle and allow the sample cell to cool to room temperature. Backfill the sample tube with helium to atmospheric pressure, remove from the degassing station, and close it with a stopper.

Sample Analysis

1. Place the sample tube containing the carbon on the nitrogen surface area analyzer.
2. Initial the experiment. The following experimental steps, necessary to attain accurate results, can be automatically determined by most automated nitrogen surface area analyzers.

2.1 Leak Test - The vacuum volumetric technique relies on precise pressure measurements to determine the surface area of carbon. Any leaks in the system will result in erroneous surface area measurements. A minimum of a 2 min leak test of the sample and P_O cells is required. Any significant pressure change in the cells over this time interval will result in the absorption of the experiment.

2.2 Transducer Linearization - If separate sample and transducer manifolds are utilized by the testing equipment, it is necessary to zero and linearize the transducers prior to each experiment.

2.3 Sample Cell Volume - In determining the void volume of the sample cell, both the warm zone and cold zone (section submersed in liquid nitrogen) must be measured prior to each analysis. Non-ideality gas corrections are applied to the volume of gas in the cold zone.

2.4 Saturated Vapor Pressure (P_0) - The saturated vapor pressure of nitrogen is affected by the purity of the liquid nitrogen and ambient pressure. Dissolved impurities in the liquid N_2 will usually cause the bath temperature to increase sufficiently to cause a 1.4 to 2.7 kPa (10 to 20 mmHg) increase in theoretical vapor pressure. Often, P_0 is assumed to be 103 kPa (775 mmHg); however, for maximum accuracy the actual P_0 should be measured.

3. Once the above conditions are measured, volumes of pure nitrogen are calculated, measured, and dosed into the sample cell. This process is repeated until equilibrium conditions are satisfied at the desired relative pressure. The summation of the dose volumes required to reach a particular relative pressure constitute the adsorption volume data at the various relative pressures. The adsorption volumes are measured at relative pressures of 0.05 to 0.30. A minimum of 5 relative pressures are recommended.

4. Backfill the sample tube at ambient temperature with helium to atmospheric pressure. Remove the sample tube from the instrument, stopper it, and weigh it to the nearest 0.0001 g and record as mass *B*.

5. Nitrogen adsorbed by the carbon at the various relative pressures is used to prepare the B.E.T. plot. The data points that give the best straight line are used to calculate the slope and y-intercept. The slope and y-intercept are used to calculate the surface area. For examples of how to select the proper relative pressure range.

6. A B.E.T. plot that yields a negative y-intercept could be indicative of the presence of microprobes (< 3 nm diameter), but others factors can produce a negative y-intercept. The surface area is calculated from the pressure range that yields the highest correlation coefficient and positive y-intercept.

Calculation

1. Calculate the sample mass as follows :

$$S = B - A$$

where :

S = sample mass, g,

A = mass of sample tube, stem, and stopper, and

B = mass of sample tube, stem, stopper, and sample after analysis.

2. Calculate the nitrogen surface area (NSA) to the nearest $0.1 \times 10^3 \text{ m}^2/\text{kg}$ ($0.1 \text{ m}^2/\text{g}$) as follows :

$$\text{NSA} = \frac{V_M N A_{CS}}{22\,400 \times S}$$

where :

N = Avagadro's number, 6.023×10^{23} molecules/mole,

A_{CS} = Cross-section area of nitrogen molecule, $16.2 \times 10^{-20} \text{ m}^2/\text{molecule}$, and

22 400 = number of cm^3 occupied by one mole of gas at STP.

สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย

Appendix C

Table C.1 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different temperatures and times (size 1.18 - 2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

Table C.2 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different sizes (900°C for 45 min, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

Table C.3 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different flow rate of CO₂ (900°C for 45 min, size 0.60 - 1.18 mm, 200 g, air 0.27 nl/min and superheated steam).

Figure C.1 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 750°C for 30 min. b. 750°C for 45 min c. 750°C for 60 min

Figure C.2 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 800°C for 30 min. b. 800°C for 45 min c. 800°C for 60 min

Figure C.3 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 850°C for 30 min. b. 850°C for 45 min c. 850°C for 60 min

Figure C.4 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 900°C for 30 min. b. 900°C for 45 min c. 900°C for 60 min

Figure C.5 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam)

a. size 0.25 - 0.60 mm b. size 0.60 - 1.18 mm c. size 2.36 - 4.75 mm

Figure C.6 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, size 0.60 - 1.18 mm, 200g, air 0.27 nl/min, and superheated steam).

a. CO₂ 2.0 nl/min b. CO₂ 10.0 nl/min c. CO₂ 15.0 nl/min

Figure C.7 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, size 0.60 - 1.18 mm, 200 g, air 0.27 nl/min, and superheated steam).

Table C.1 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different temperatures and times (size 1.18 - 2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

T (°C)	t (min)	S _{Langmuir} (m ² /g)	Volume (cm ³ /g)			Pore diameter (Å)
			V _{Micro}	V _{Non-micro}	V _{Total}	
750	30	486.47	0.0575	0.2781	0.2356	28.87
	45	503.41	0.0963	0.2827	0.3790	28.32
	60	659.04	0.1306	0.2953	0.4259	27.46
800	30	637.33	0.1262	0.2928	0.4210	27.61
	45	699.13	0.1349	0.2993	0.4342	26.74
	60	805.27	0.1713	0.3181	0.4894	24.21
850	30	768.05	0.1601	0.3036	0.4637	25.15
	45	793.22	0.1732	0.3132	0.4864	23.62
	60	832.25	0.1741	0.3157	0.4898	23.35
900	30	826.61	0.1720	0.3219	0.4939	24.07
	45	863.73	0.1827	0.3342	0.5169	22.63
	60	856.20	0.1775	0.3290	0.5065	23.12

Table C.2 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different sizes (900°C for 45 min, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

Tires char sizes (mm)	S _{Langmuir} (m ² /g)	Volume (cm ³ /g)			Pore diameter (Å)
		V _{Micro}	V _{Non-micro}	V _{Total}	
0.25 - 0.60	692.66	0.1319	0.3027	0.4346	27.15
0.60 - 1.18	878.59	0.1996	0.3259	0.5255	22.38
1.18 - 2.36	863.73	0.1827	0.3342	0.5169	22.63
2.36 - 4.75	520.04	0.1135	0.2751	0.3886	28.15

Table C.3 Langmuir surface area, pore volume and pore diameter of activated carbon from used tires at different flow rate of CO₂ (900°C for 45 min, size 0.60 - 1.18 mm, 200 g, air 0.27 nl/min and superheated steam).

CO ₂ (nl/min)	S _{Langmuir} (m ² /g)	Volume (cm ³ /g)			Pore diameter (Å)
		V _{Micro}	V _{Non-micro}	V _{Total}	
0.0	963.93	0.2119	0.3512	0.5631	22.17
2.0	890.55	0.2041	0.3318	0.5359	22.24
5.0	878.59	0.1996	0.3259	0.5255	22.38
10.0	869.46	0.1847	0.3195	0.5042	22.53
15.0	847.21	0.1829	0.3146	0.4975	22.85

สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย

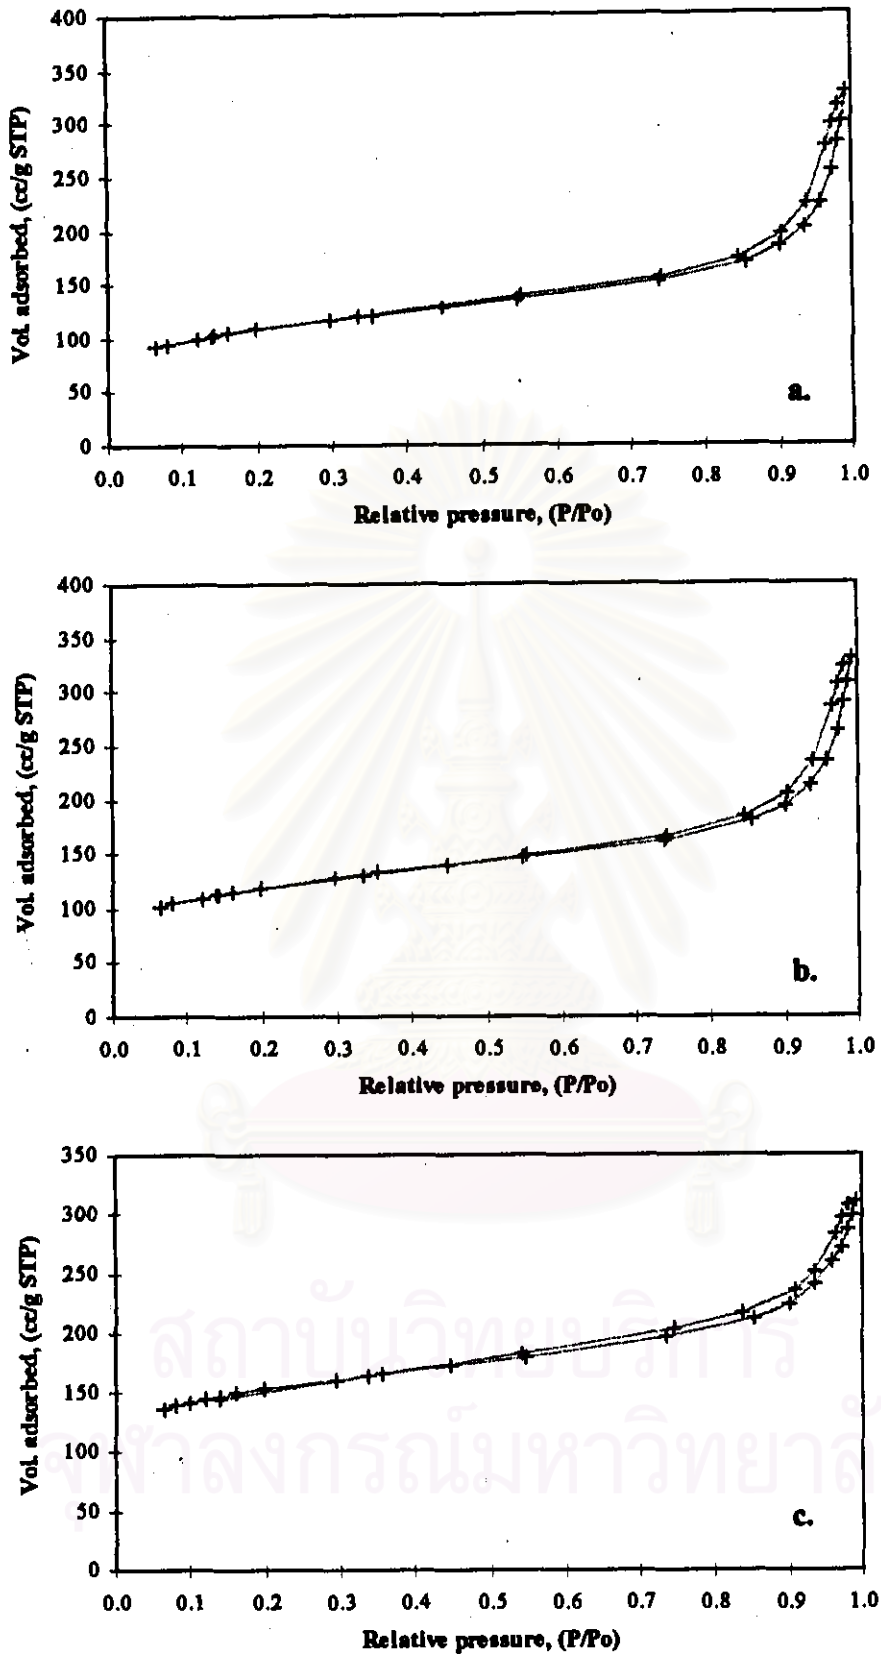


Figure C.1 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 750°C for 30 min

b. 750°C for 45 min

c. 750°C for 60 min

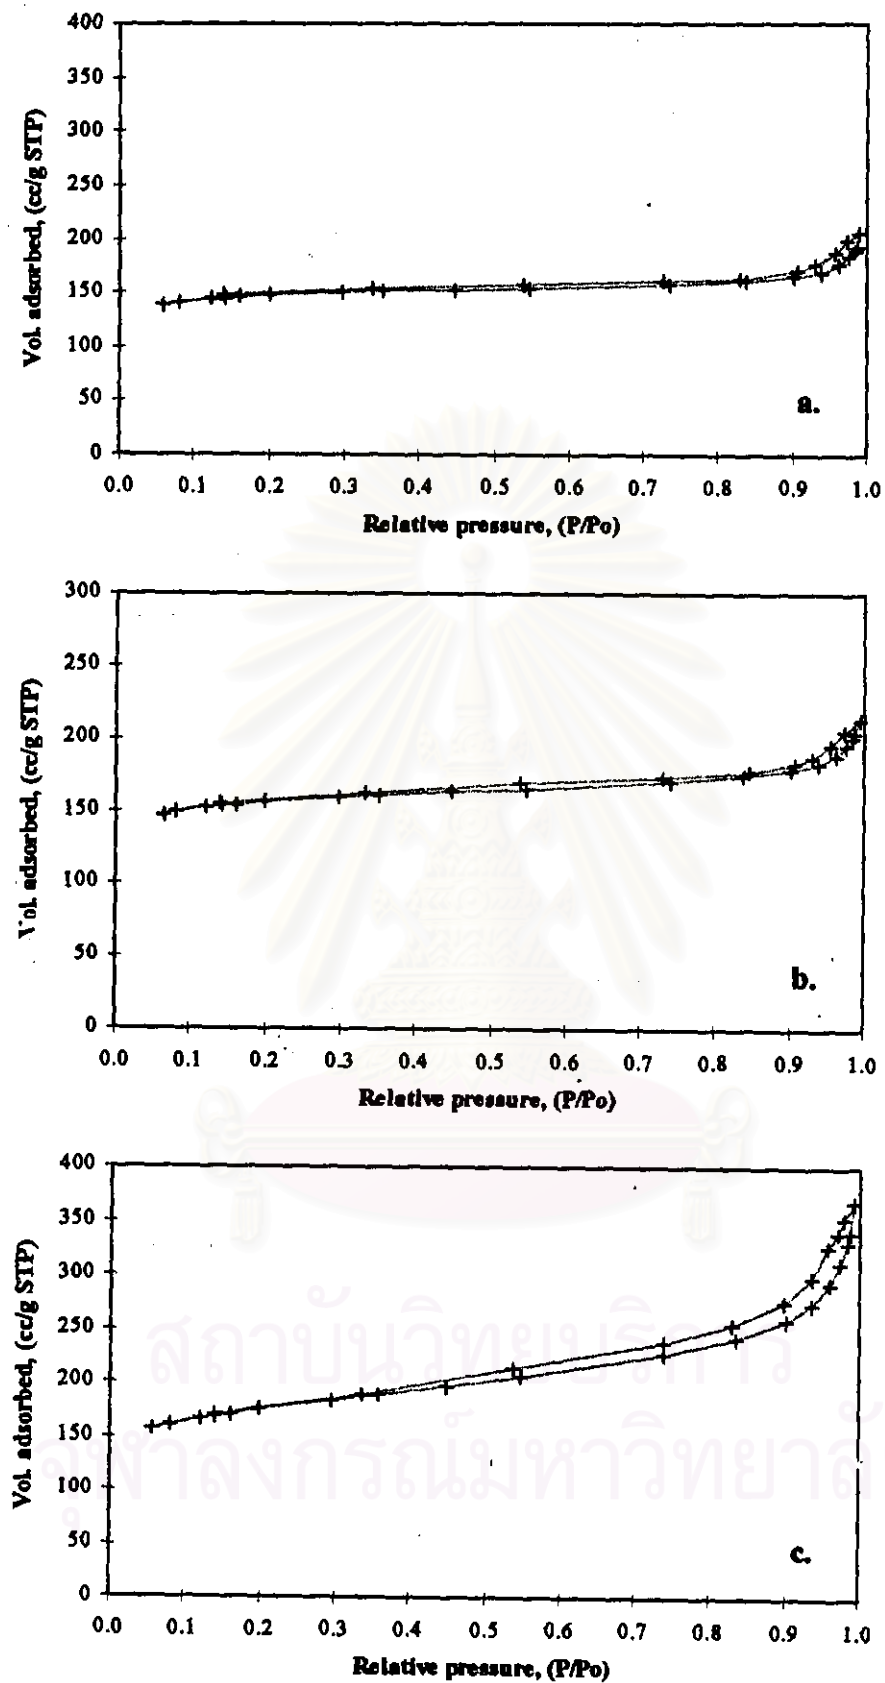


Figure C.2 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 800°C for 30 min

b. 800°C for 45 min

c. 800°C for 60 min

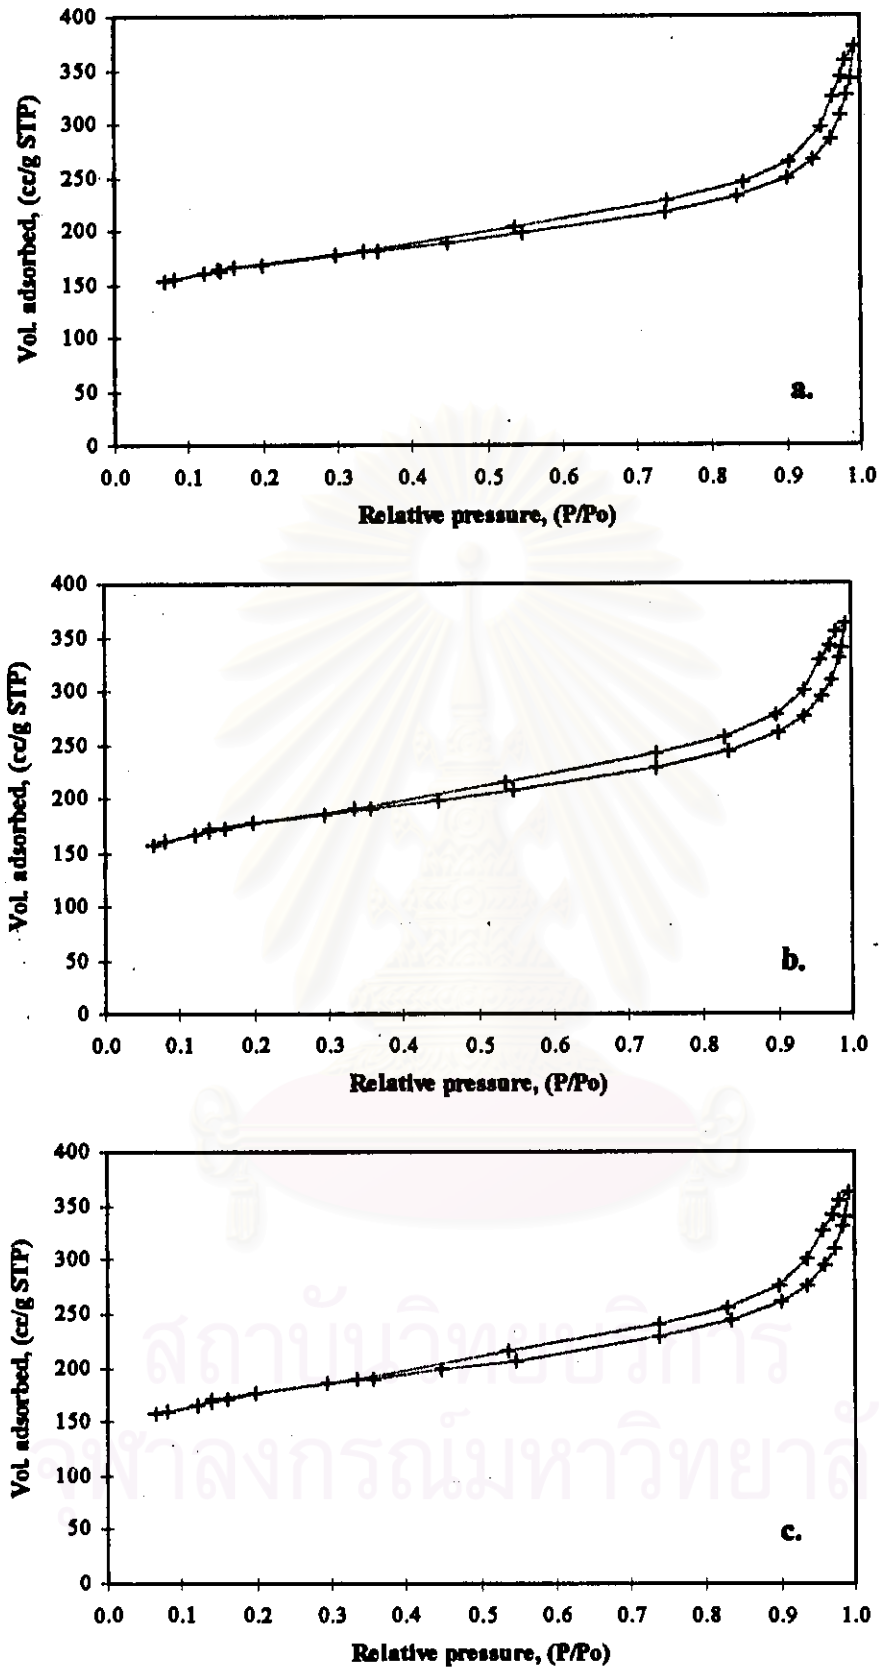


Figure C.3 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 850°C for 30 min

b. 850°C for 45 min

c. 850°C for 60 min

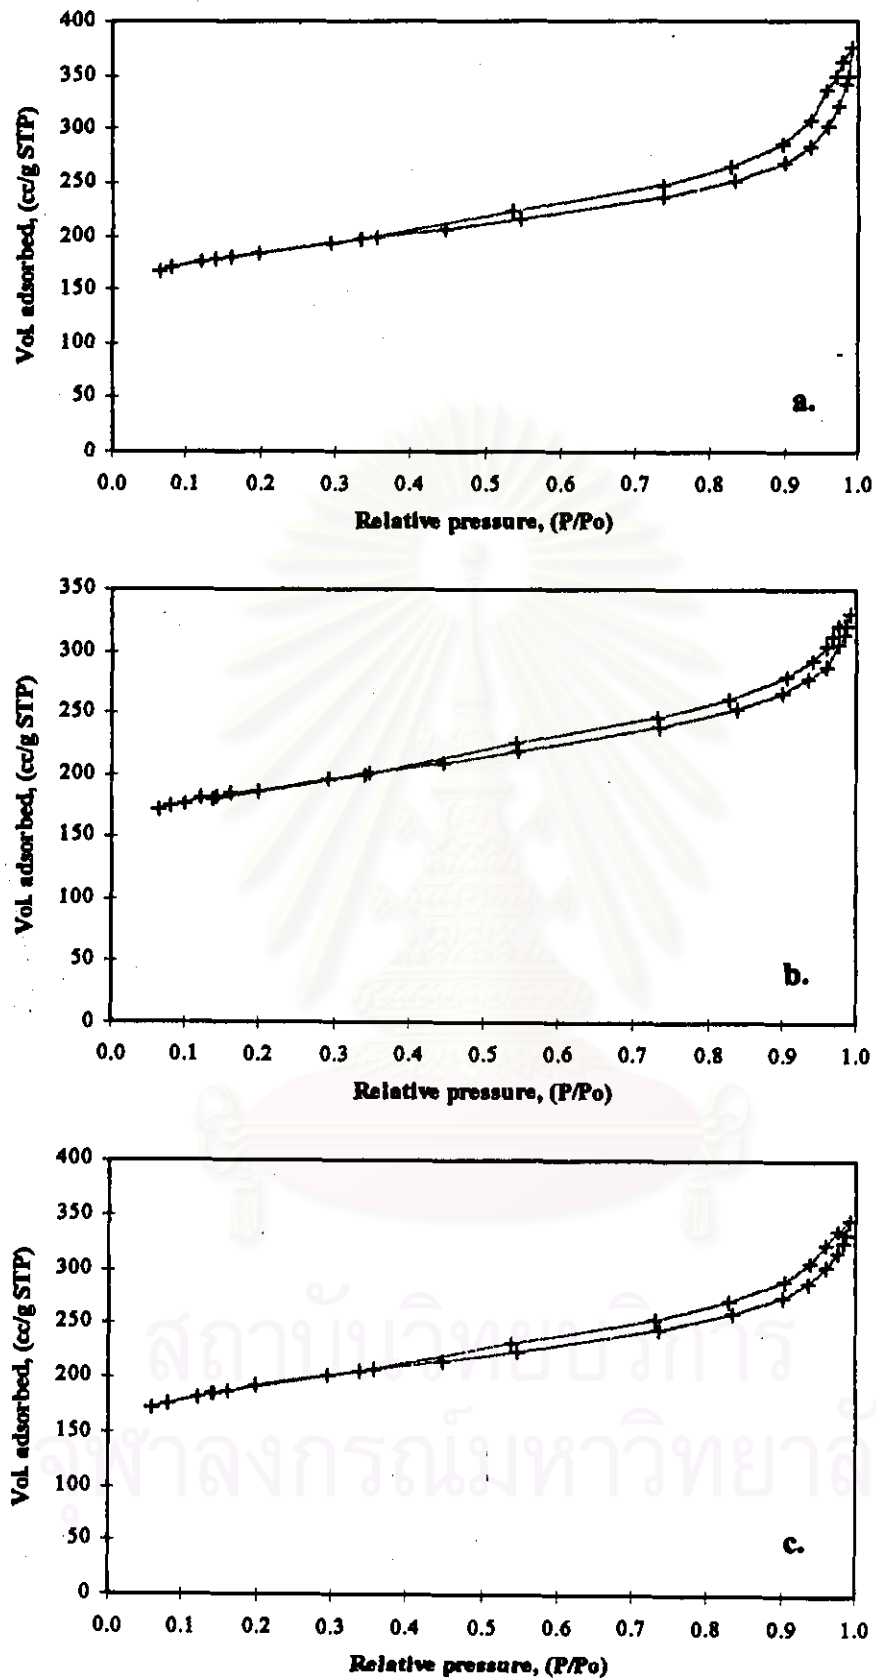


Figure C.4 Adsorption and desorption isotherm of activated carbon from used tires (size 1.18-2.36 mm, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. 900°C for 30 min

b. 900°C for 45 min

c. 900°C for 60 min

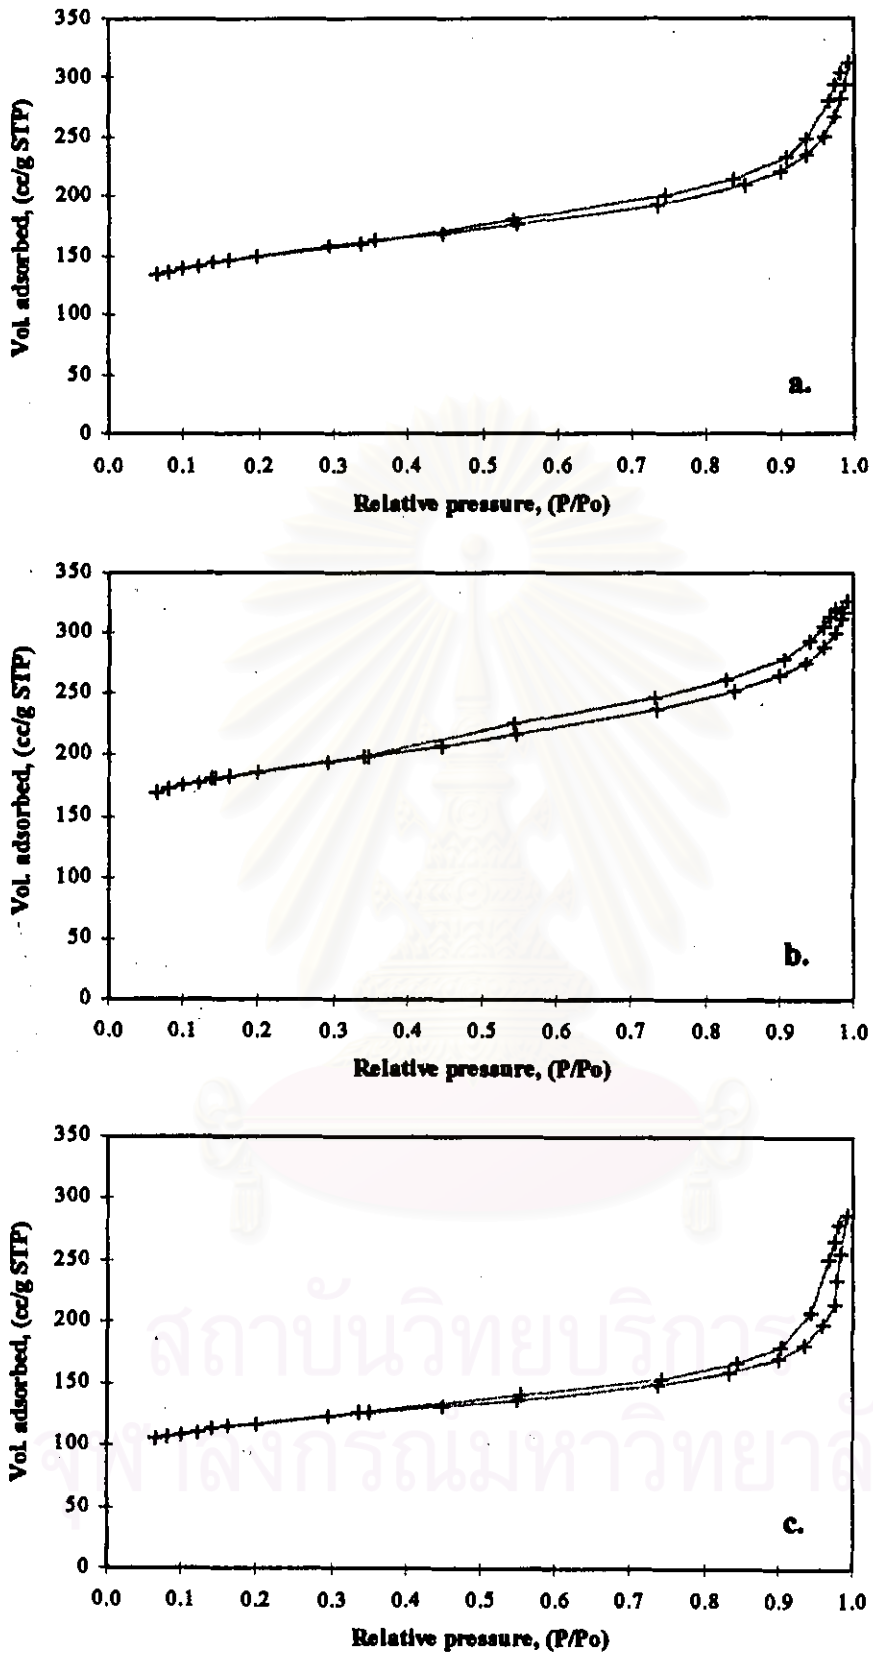


Figure C.5 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, 200 g, air 0.27 nl/min, CO₂ 5.0 nl/min and superheated steam).

a. size 0.25 - 0.60 mm

b. size 0.60 - 1.18 mm

c. size 2.36 - 4.75 mm

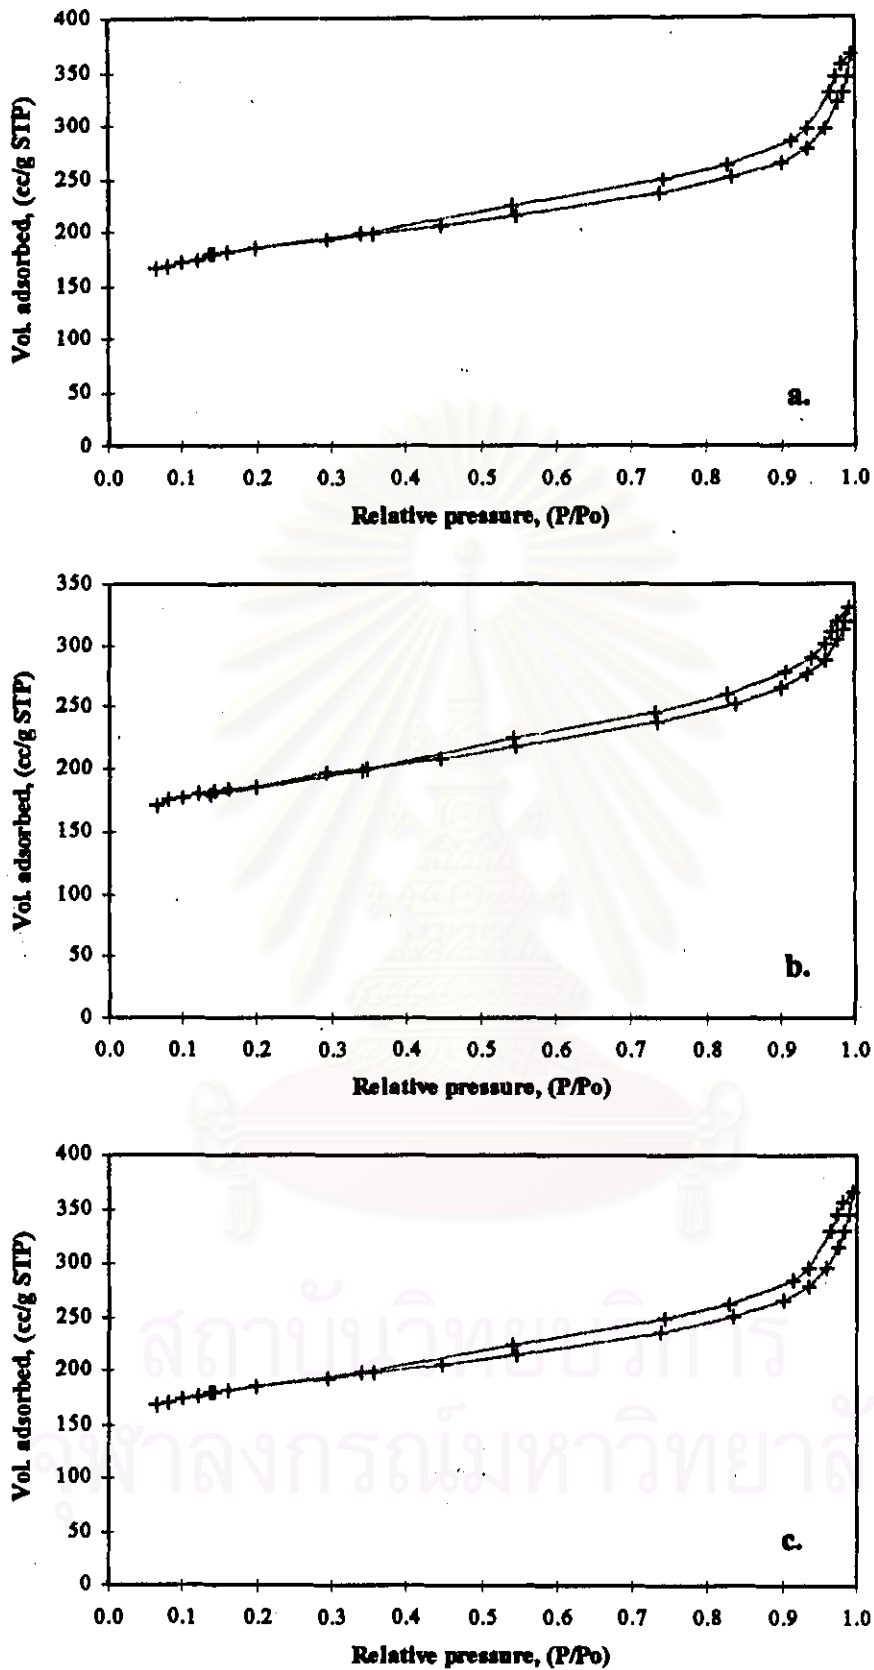


Figure C.6 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, size 0.60 - 1.18 mm, 200g, air 0.27 nl/min, and superheated steam).

a. CO₂ 2.0 nl/min

b. CO₂ 10.0 nl/min

c. CO₂ 15.0 nl/min

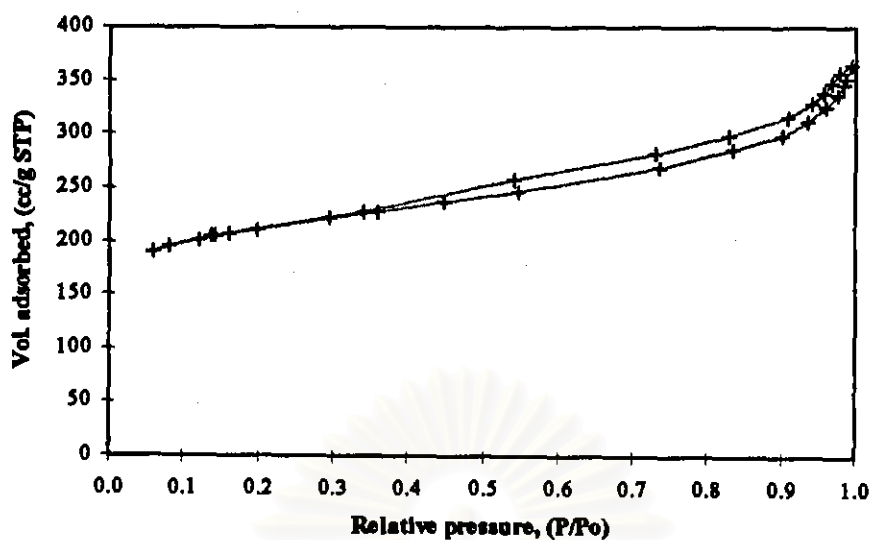


Figure C.7 Adsorption and desorption isotherm of activated carbon from used tires (900°C for 45 min, size 0.60 - 1.18 mm, 200 g, air 0.27 nl/min, and superheated steam).

สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย

VITA

Thanapon Lortong was born on June 10, 1975 in Samutsongkhram, Thailand. She received Bachelor Degree of Science of Chemistry at Chulalongkorn University in 1994. She continued her Master's study at Petrochemical and Polymer Science Department, Graduate School, Chulalongkorn University in 1995 and completed the program in 1998.



สถาบันวิทยบริการ
จุฬาลงกรณ์มหาวิทยาลัย